

# CARBON STEELS

## Section 12 - Welding Consumables

<b>Carbon Steels</b>	1
Welding of Carbon Steels	2
MMA Electrodes	24
MIG/MAG Wires	43
MIG & TIG Wires for CMn & Low Alloy Steels	49
Flux & Metal Cored Wires	50
Cored Wires for CMn & Low Alloy Steels	59
Subarc Wires & Fluxes	62
Submerged Arc Fluxes	66
Oxy-Fuel & Gas Welding Rods	69


# Welding of Carbon Steels

## Weldability of Steel

Weldability is a term used to describe the relative ease or difficulty with which a metal or alloy can be welded. The better the weldability, the easier it is to weld. However, weldability is a complicated property, as it encompasses the metallurgical compatibility of the metal or alloy with a specific welding process, its ability to be welded with mechanical soundness, and the capacity of the resulting weld to perform satisfactorily under the intended service conditions.

Before attempting to weld any material, it is essential to know how easy it is to weld and to be aware of any problems that might arise. One of the main problems likely to be encountered when welding carbon and alloy steels is hydrogen cracking. For hydrogen cracking to occur, it is necessary to have a supply of hydrogen to the weld and a heat affected zone (HAZ), a susceptible hardened microstructure, and tensile stress. If any one of these three components is eliminated, then hydrogen cracking will not happen. Solidification cracking and lamellar tearing are other potential problems associated with welding steel.

The main problem when welding steel is hardenability. As long as the steel contains sufficient carbon when it is cooled rapidly from high temperature, a phase transformation takes place. The phase transformation from austenite to martensite causes the material to harden and become brittle. It is then liable to crack on cooling, due to restraint, or later under the action of hydrogen.

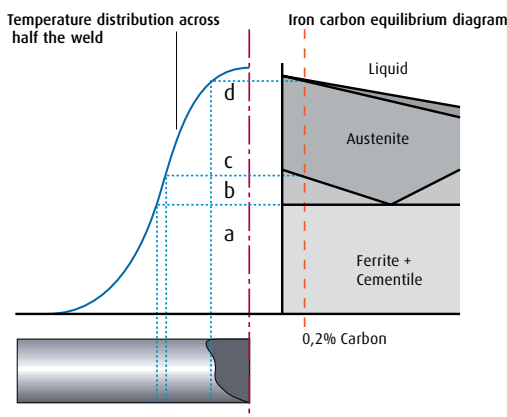

Variation in temperature from the centre of the weld to the base material

The weldability of steel depends primarily on its hardenability and this, in turn, depends largely on its composition (most importantly its carbon content). Steels with carbon content under 0,3% are reasonably easy to weld, while steels with over 0,5% are difficult. Other alloying elements that have an effect on the hardenability of steel, but to a much lesser extent than carbon, are manganese, molybdenum, chromium, vanadium, nickel and silicon. These, together with carbon, are all generally expressed as a single value (the carbon equivalent). The higher the carbon equivalent, the higher the hardenability, the more difficult the steel is to weld, and the more susceptible the microstructure is likely to be to hydrogen cracking.

This effect can be overcome by preheat combined with the use of a low hydrogen process or low hydrogen welding

consumables. Calculation of preheat is usually based on carbon equivalent (derived from steel composition), combined thickness of the components, and heat input from the welding process. It also takes account of the amount of hydrogen likely to be introduced into the weld metal by the welding process. If welding under high restraint, extra preheat may need to be applied. Some high carbon steels and low alloy steels may also need a post weld stress relief or tempering.

## Hardenability and Hardness

To become harder, steel must undergo a phase change. The starting point is austenite, so the steel must first be heated into the austenitic temperature range (see diagram on left).

- Austenite, quenched rapidly, will be transformed into martensite, a hard but brittle phase
- A slower cooling rate will promote formation of bainite and/or other softer phases
- Cooled even more slowly, a soft structure of ferrite plus cementite, called perlite, results.



Martensite, tempered martensite and heavily tempered martensite

## Hardenability

Hardenability is the potential for any particular steel to harden on cooling and, as the carbon content of the steel increases towards 0,7%, so the potential of the steel to harden increases. Increasing the alloy content of the steel also increases the hardenability.

While hardness and strength may be desirable in a welded steel structure, martensite can be brittle and susceptible to cracking, and it should be noted that the potential brittleness of the material also increases as hardenability increases.

Hardenability describes the potential of steel to form hard microstructures. What hardness is actually achieved in steel with known hardenability depends on the maximum temperature to which it is heated and the cooling rate from that temperature. During welding, the parent material close to the weld will be heated to temperatures near melting point, while further away it will remain at ambient temperature. The cooling rate depends on the mass of material, its temperature, and the welding heat input. Therefore, when welding any given hardenable steel, the hardness in the HAZ depends on the cooling rate – the faster the cooling rate, the harder the microstructure produced and the more susceptible it is to cracking.



After welding, the hardness in the HAZ may range from less than 300 HV to more than 550 HV, depending on the parent steel composition and the other factors described above. As the hardness of the HAZ increases, so does its susceptibility to hydrogen cracking. However, as a rule of thumb, if the maximum hardness in the HAZ is maintained below 350 HV, then hydrogen cracking will be avoided.

### Carbon Equivalent

Carbon has the greatest effect on the hardenability of steel, but other alloying elements may be added to increase its hardenability. The addition effectively reduces the critical cooling rate and the temperature at which the austenite to martensite transformation takes place, making it easier for martensite to form at slower cooling rates.

Alloying elements that have the greatest influence on the hardenability of steel are manganese, molybdenum, chromium, vanadium, nickel, copper and silicon, but they have a much smaller effect than carbon.

The effect of these elements on the tendency to form HAZ martensite, and hence the likelihood of hydrogen cracking, is expressed conveniently as a carbon equivalent (CE). This basically describes the influence of each element on hardenability in terms of the effect that carbon has. There have been many different formulae derived to express carbon equivalent, but the one quoted here is the International Institute of Welding (IIW) equation that is applicable to carbon steel and is widely used:

#### Carbon equivalent (CE) =

$$\%C + \frac{\%Mn}{6} + \frac{(\%Ni + \%Cu)}{15} + \frac{(\%Cr + \%Mo + \%V)}{5}$$

The equation is only valid for certain maximum percentages of each element and these percentages can be found in the technical literature.

The carbon equivalent is used mainly for estimating preheat. Preheat is necessary to slow down the cooling rate sufficiently to reduce hardening in the HAZ of welds in susceptible carbon and low alloy steels. This, in turn, helps to prevent subsequent HAZ hydrogen cracking. The overall effect is to improve the weldability of the steel being welded, or at least to overcome the weldability problems presented by it.

CE is calculated from the composition of the steel in question and is used – together with welding heat input, potential hydrogen from the consumable, and combined thickness, or by reference to published data – to determine the preheat. It is recommended that the actual composition of the steel is used to ensure accuracy of calculation of CE, but nominal or maximum specified compositional data may be used when

this is unavailable. The use of nominal composition obviously carries some risk that CE will be underestimated and too low preheat will be used, with potential cracking problems.

### Weldability

Weldability describes the relative ease or difficulty with which a metal or alloy can be welded.

The relative weldability of carbon and low alloy steels are summarised here.

As has already been stated, weldability varies with the chemistry of the steel, particularly with reference to its carbon content.

The majority of carbon steels are weldable, but some grades have better weldability and, therefore, are more easily welded than others. As the carbon content increases, weldability tends to decrease as the hardenability increases and the steel becomes more prone to cracking.

Low carbon steels containing <0,15% carbon and <0,6% manganese generally have good weldability, as the composition is too lean to give any significant hardening effect during welding. However, steels with <0,12% carbon and low levels of manganese can be prone to porosity, although they are not susceptible to hydrogen cracking.

Steels with carbon contents between 0,15 and 0,3% carbon and up to 0,9% manganese, have good weldability, particularly those with carbon content below 0,22%. These are mild steels and rarely present problems, as long as impurity levels are kept low. They are all weldable without preheat, using any of the common welding processes. Those at the top end of the composition range, above about 0,25% carbon, may be prone to cracking under certain circumstances. They may be welded using any of the common welding processes, but are best welded with a low hydrogen process such as MIG or low hydrogen consumables. Thick sections may require preheating to reduce the cooling rate.

Medium carbon steels containing between 0,25 and 0,5% carbon, with generally <1% manganese, are hardenable by heat treatment and so are prone to cracking when welded. They can be welded, but require suitable welding procedures, specifying preheat and interpass temperature control to account for the carbon content or carbon equivalent and the combined thickness of the joint being produced. These steels should always be welded using a low hydrogen welding process or controlled hydrogen consumables.

Steels with even higher carbon levels, between 0,5 and 1,0%, with <1% manganese, are used where their higher hardness and strength can be exploited. However, their high hardenability means that they have poor weldability and are difficult to weld without cracking. They are generally welded in the hardened condition and so require preheating, interpass temperature control and post weld stress relief to give any chance or avoiding cracking. Low hydrogen processes, such as MIG and TIG welding or low hydrogen consumables, such as low hydrogen MMA electrodes will always be required when welding these steels.

Carbon-manganese steels have carbon typically between 0,15 and 0,5%, and manganese levels between 1,0 and 1,7%. For structural purposes, carbon is normally held below 0,3%, manganese not above 1,2% and sulphur and phosphorous are required to be below 0,05%. Generally, they are weldable, although some will require controls on preheat and heat input. Those at the higher end of the carbon range also benefit

from the use of low hydrogen welding processes or controlled hydrogen consumables.


Structural steels often have limits imposed on maximum carbon equivalent to ensure good weldability and ease of welding for the fabricator.

Weldable high strength low alloy (HSLA) steels have weldability similar to the low carbon steels, and so do not usually present problems.

Most quenched and tempered steels can be welded, but they rely on relatively high cooling rates for the strong martensitic structures to form. Careful control of preheat, heat input and interpass temperature is required to achieve the correct structure without cracking. Welding must be carried out using a low hydrogen process, or hydrogen-controlled consumables, and welding procedures need to be tested and approved.

### Weld and HAZ Cracking


With steel, poor weldability often manifests in a reduction of the resistance of the steel to cracking after welding.

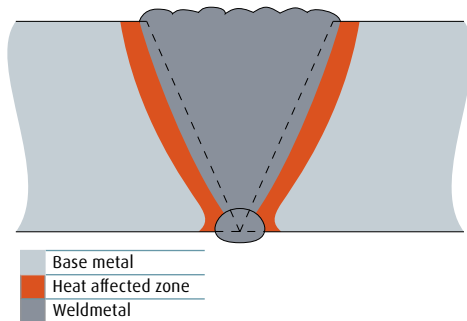

The main causes of cracking in steel are:

- High levels of carbon and other alloy elements, resulting in brittle zones around the weld
- High cooling rates after welding increasing the hardness, which increases the susceptibility to cold cracking
- Joint restraint preventing contraction after welding, leading to cracking
- Hydrogen in the weld bead or HAZ, leading to hydrogen-induced cold cracking
- Contaminants like sulphur and phosphorous, resulting in solidification cracking
- Lamellar tearing due to inclusions layering during rolling, resulting in deterioration of the through-thickness properties.

The most common cause of cracking in steel is the presence of hydrogen. Hydrogen (or cold) cracking is usually considered the most serious potential problem with modern steels. Hydrogen cracking is most frequently a HAZ phenomenon, but it can also occur in weld metal, particularly in high alloy steels. Hydrogen, like carbon, is more soluble in austenite than ferrite and can easily be picked up by the weld metal. When ferrite is formed as the material cools, hydrogen solubility decreases and hydrogen diffuses to the HAZ, where it becomes trapped and can cause crack propagation.

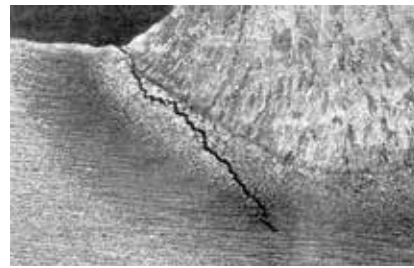

### Heat affected zone (cold cracking)

There are published guidelines and standards that contain welding procedures to avoid hydrogen cracking. For hydrogen cracking to occur, it is necessary to have a supply of hydrogen to the weld and HAZ, a susceptible hardened microstructure, and tensile stress. If any one of these three components is eliminated, then hydrogen cracking will not happen.

To avoid cold cracking, the following points should be noted:

- The lower the carbon equivalent, the lower the potential for cracking
- Limit the hydrogen content of weld metal and HAZ by using a low hydrogen process or low hydrogen consumables
- Keep joint restraint to a minimum by careful joint design
- Reduce the cooling rate of the weld area by preheat and suitable welding heat input
- Eliminating hydrogen after the weld is completed by keeping the weld hot (hydrogen release treatment)
- Ensure impurities are kept at a low level.

The above guide is of a very general nature. If in doubt, seek expert technical advice.

### Factors Influencing Weldability

In terms of avoiding weldability problems, particularly hydrogen cracking, when welding carbon or low alloy steels, there are several factors that demand consideration. These include the amount of hydrogen generated by the welding process or consumable, the heat input into the weld, the combined thickness (heat sink) of the joint, and the level of preheat applied to the components prior to welding. Joint configuration and restraint are also important factors when considering weldability.

### Process Hydrogen

One of the three key components necessary for hydrogen cracking is a source of hydrogen. During welding, the most likely sources of hydrogen are the welding consumables or contaminants on the parent material. Here we consider hydrogen from the welding process and consumables only.

The amount of hydrogen put into the weld will vary from one welding process to another and may also vary within a process from one consumable type to another. The risk of hydrogen cracking increases as the amount of hydrogen from the process or consumable gets larger.

Solid wire processes, such as MIG and TIG, are capable of giving hydrogen levels below 5 ml/100 g of weld metal. These are generally thought to be low hydrogen processes, provided the MIG wire is clean.

The manual metal arc process can give a wide range of hydrogen levels, from well over 15 ml/100 g of weld metal (with cellulosic and rutile coated electrodes) to less than 5 ml/100 g of weld metal (with basic coated electrodes) given the appropriate baking or re-drying treatment.

The potential hydrogen levels can vary with product type for cored wire welding processes too. Basic type flux cored wires may be capable of getting below 5 ml/100 g of weld metal, but rutile cored and metal cored wire types may give 10 or 15 ml/100 g of weld metal. Some recent developments have enabled metal cored and rutile cored wire to achieve hydrogen levels below 10 ml/100 g, with some even below 5 ml/100 g.

Submerged arc wires, like MIG wires, should be able to give low levels of hydrogen but, when used in combination with different fluxes, the hydrogen level may vary between <5 to 15 ml/100 g of weld metal.

### Welding Heat Input

The heat input from the welding process plays a major role in the heating and cooling cycles experienced by the weld and parent plate during welding. For a given plate thickness, a high heat input is likely to result in a slower cooling rate than a low heat input, and will therefore produce a softer microstructure in the HAZ that is less prone to hydrogen cracking. However, that does not mean that welding should always be carried out with a high heat input, because this brings with it other problems, such as loss of mechanical properties and an increased risk of solidification cracking. So it is necessary to select a heat input to give a sound weld with the desired mechanical properties and to use preheat to exert control of the cooling rate.

Heat input 'Q' may be calculated as:

$$Q = \frac{k \times V \times I \times 60}{S \times 1\,000} \quad \text{kJ/mm}$$

where 'V' is arc voltage (V), 'I' is welding current, and 'S' is welding speed in mm/min.

The value derived from this formula may be multiplied by a factor 'k', the thermal efficiency factor for the welding process, to give an energy input that takes the efficiency of the welding process into account. Typical thermal efficiency factors are:

- 'k' = 1,0 for submerged arc welding
- 'k' = 0,8 for MIG/MAG, MMA, flux cored and metal cored arc welding
- 'k' = 0,6 for TIG and plasma welding

For example, when MIG welding, the welding heat input formula becomes:

$$Q = \frac{0,8 \times V \times I \times 60}{S \times 1\,000} \quad \text{kJ/mm}$$

Welding heat input will vary with process and consumable type and size. With small diameter electrodes, low current and fast welding speeds, heat inputs below 1,0 kJ/mm are readily attained. With large diameter electrodes, high currents and slower welding speeds, heat inputs in excess of 6,0 kJ/mm can be reached.

Note that a weld made using a stringer bead technique will have a lower heat input than a weld made with the same size electrode at the same current but using a weave bead technique.

### Combined Thickness


The cooling rate of plate in the region of a weld depends on the thickness of the plates in the joint, the number of plates meeting at the joint, the amount of heat put into the weld area, and the initial temperature of these plates. Cooling occurs by conduction and so the greater the heat sink, the faster the cooling rate. Therefore, other factors being constant, the thicker the plate, the greater the potential for rapid cooling, and so the greater the likelihood of hardening in the HAZ of susceptible steels.

Estimates of preheat will normally take into account the thickness of each of the components in the joint to allow for the cooling effect. The thickness of each component is added together to give what is normally referred to as 'combined thickness' (CT).


How the combined thickness is derived depends on the joint configuration and is illustrated below:

$$CT = T_1 + T_2 + T_3 \dots$$

#### Example of combined thickness calculation for butt joint

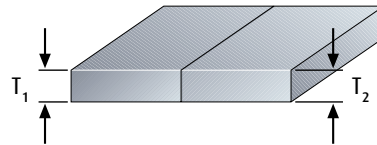

#### Example of combined thickness calculation for fillet joint

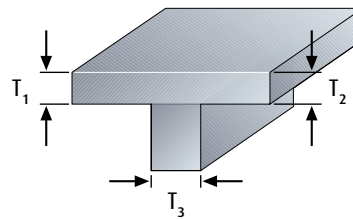

For butt welds, the CT equals the sum of the thicknesses of the two plates being welded; for fillet welds, the CT equals twice the thickness of the base plate plus the thickness of the up-stand. Therefore, for a given plate thickness, a fillet joint has a faster cooling rate than a butt joint.

## Recommendations for the Storage, Handling and Treatment of Afrox Hydrogen Controlled Basic Carbon Steel Electrodes

### Handling

Afrox electrodes are packed in cardboard cartons with a moisture resistant polythene wrapping. Further protection is provided by shrinking these rigid cartons into packs of three.

The packs are stacked to a maximum of eight high on wooden pallets.

This is the recommended maximum height to avoid crushing and hence possible damage during storage.

### Storage

Basic low hydrogen electrodes should be stored in dry conditions, off the floor on pallets or racks in their unopened containers. The rate of moisture re-absorption which takes place is determined by the resistance of the electrode to the atmospheric conditions of relative humidity and temperature prevailing during storage.

Storage is not really the most important issue in determining subsequent weld metal hydrogen content of low hydrogen electrodes, but rather, the rate at which moisture is lost during re-baking of electrodes prior to use.

Storage under the correct conditions will provide indefinite product shelf-life.

### Re-baking

It is essential that hydrogen-controlled electrodes be re-baked prior to use. The re-baking temperature recommendations depend on the maximum permissible hydrogen content tolerable in the deposited weld metal and the hardenability of the parent material.

Standard Re-baking Temperatures		
Product	5-10 ml H <sub>2</sub> /100 g	<5 ml H <sub>2</sub> /100 g
7018-1	350 - 370°C	-
78MR	250 - 270°C	370 - 400°C
Ferron 1	350 - 370°C	-
Baking time one-two hours		
Diffusible hydrogen content determined using Yanaco gas chromatograph		

Optimum conditions for re-baking are achieved when electrodes are placed on the oven shelves not more than five deep. This is normally only required when diffusible hydrogen contents of less than 5 ml H<sub>2</sub>/100 g of weld metal are specified and hardenable materials in thick sections have to be welded.

For general shop conditions, the electrode pile in the oven can be increased provided consumables in the centre of the pile achieve the minimum re-baking temperature for a minimum period of one hour.

Note: When electrodes are placed in a baking oven, the temperature in the electrode pile rises far more slowly

than it takes for the oven's own temperature to rise to the set temperature. It is therefore incorrect to take the oven temperature as an accurate indication of the actual baking temperature reached by the electrodes and hence a guide to the time at temperature.

Unless the temperature during baking is timed on the basis of the electrode temperature, the electrodes cannot be considered properly re-baked prior to use.

If possible, it is recommended that fabricators carry out checks on their re-drying ovens to establish the correct conditions for actual electrode re-baking temperatures and times as compared to oven temperatures and times.

It is important to note that if the electrodes are maintained at the re-bake temperature for long periods of time, the coating may become brittle. Coating brittleness may also result if the electrode is re-baked above the maximum recommended temperature.

### Number of Re-bakes

Repeated re-baking has an adverse effect on electrode coating strength and adhesion to the core wire. From tests carried out by Afrox, it is recommended that:

Re-baking at 370-400°C be limited to two times and re-baking at 250-270°C be limited to three times. (This does not include the factory bake).

### Holding Conditions

Immediately after baking, the electrodes should be transferred to a holding oven alongside the baking oven. The recommended holding temperature is 150°C ± 20°C. The holding time is virtually indefinite with a working limit suggested as 120 hours. Any electrodes that are inadvertently exposed to excessive moisture, rain, etc. or are damaged, should be removed from the work site and destroyed.

### Quivers

Electrodes drawn from holding ovens should be held in heated quivers at a minimum temperature of 75°C. The suggested period for the electrodes to remain in the quivers is eight hours. After this time, any remaining electrodes should be returned for re-baking.


### General

In some instances, it may be possible to modify the above requirements, depending on the type of work which is being undertaken and technical requirements being imposed. Please refer any technical queries to the Marketing Department, Afrox Welding Consumables on (011) 490 0400.

## Preheating of Materials

### What is Preheat?

A heating procedure applied to parent metal components immediately before welding commences, and considered as an essential part of the welding operation, is called 'preheat'.

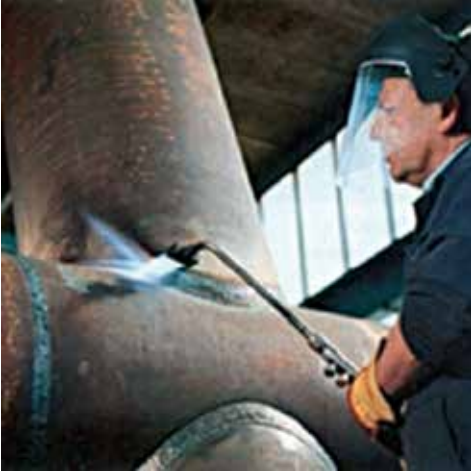

Preheating can be applied locally to the areas to be welded, or to the whole component. It is usually done to raise the temperature of the weld area so that the weld does not cool too quickly after welding. This protects the material being welded from the various adverse effects that can be caused by the normally rapid cooling cycle created by the welding process.

Note that, while preheat is applied before welding begins, it is essential that the minimum preheat temperature is maintained throughout the welding operation.

### What Does Preheat Do?

Basically, preheat puts the parent metal components in a suitable condition for the subsequent welding operation. Preheating may be carried out for any of the following reasons:

- Slow down the cooling rate
- Reduce shrinkage stress and weld distortion
- Promote fusion
- Remove moisture.

### Slow down the cooling rate

Some alloys (notably high carbon and low alloy steels), if welded and allowed to cool quickly, can develop hard or brittle phases in the heat affected zone (HAZ). These phases can render such alloys susceptible to cracking under the action of tensile shrinkage stresses as the weld area cools down, or they can result in low toughness of the HAZ.

Many steels are susceptible to hydrogen cracking, and fast cooling rates not only promote the formation of hard, susceptible microstructures but also lock the hydrogen into the solidifying weld metal. Because of this trapped hydrogen gas, pressure builds up in the weld and the heat affected zone, which can result in cracking of the already brittle microstructure. Such cracks are normally detected by post weld inspection techniques, but should they escape detection, they may lead to premature failure in service, with potentially disastrous consequences.

Preheating of components prior to welding in these situations is designed primarily to slow down the rate of cooling of the weldment. In reducing the cooling rate, preheat is protecting the parent metal by helping to prevent hardening of the weld by the formation of brittle phases. A softer, more ductile structure is more resistant to cracking. The slower cooling rate also gives more time for any hydrogen introduced into the weld to diffuse away from the welded joint.


### Reduce shrinkage stress and weld distortion

If welds are made in highly restrained joints, or in materials with very low ductility (e.g. cast irons), the welding cycle of heating, followed by rapid cooling, can result in cracking in the weld or the surrounding area. This is due to the weld metal or adjacent parent metal not being able to withstand the effects of shrinkage stresses created by contraction.




### Metals and alloys that should not be preheated

Preheat and high interpass temperatures can have a negative effect on the mechanical properties or corrosion resistance of some alloys. For example:

- Austenitic manganese (13% Mn) steel
- Austenitic stainless steels
- Duplex stainless steels
- Titanium alloys.

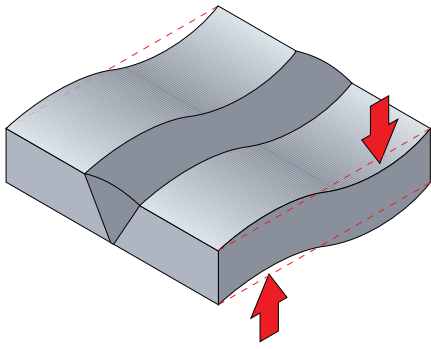

Residual stresses present in a welded joint

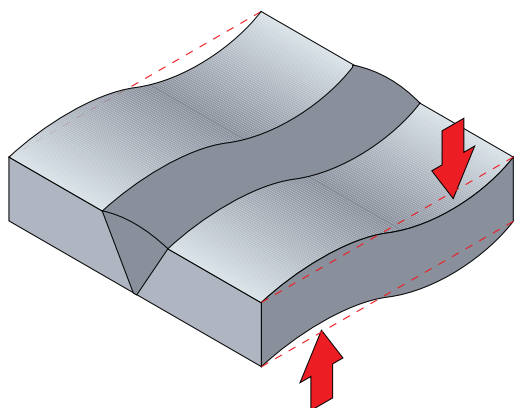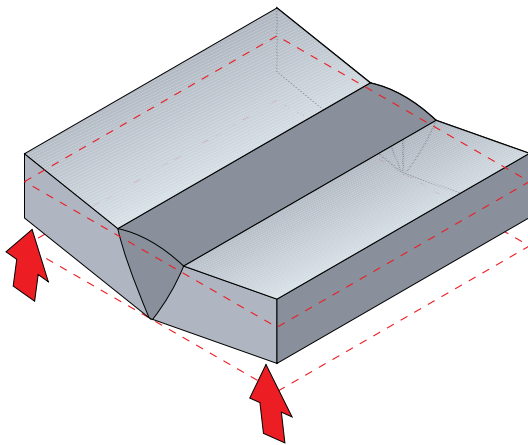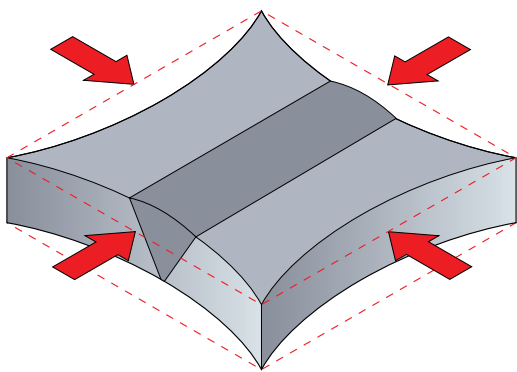

Distortion due to the presence of residual stress

Here preheating is used to balance the thermal cycle and so reduce the shrinkage stresses in the weld and in the adjacent parent material.

When welding wrought materials in highly restrained joints, preheat is normally applied locally in the weld area.

When welding castings, the preheat applied may be 'local' (heating in the area of the weld only), 'total' (the whole casting is heated), or 'indirect' (heating a part of the casting away from the weld area to balance the effects of expansion and contraction).

#### Promote fusion

Some alloy systems (e.g. copper and aluminium) have very high thermal conductivity, and if a weld is attempted on thick, cold plate, the parent material could chill the deposited weld metal so quickly that it does not fuse with the parent metal. This may be referred to as a 'cold start'. The heat conduction away from the joint area can be such that a weld may be impossible using a conventional arc welding process.

Preheat is used in this case to raise the initial temperature of the material sufficiently to ensure full weld fusion from the start. This is particularly important when using a welding process / plate thickness combination that is likely to produce a cold start.

#### Remove moisture

Any metallic components left overnight in a cold workshop or brought in from outside are likely to be damp or even wet. If they are welded in that condition, problems can arise in the resultant welds. For example, if the components are made of steel, then the moisture will act as a source of hydrogen and the result could be hydrogen cracking. Aluminium has a porous oxide layer, which will absorb moisture from the atmosphere, and, if not removed before welding, this can result in weld metal porosity and subsequent rejection of the weld.

While not normally the main objective of preheating, its use for removal of surface moisture prior to welding is not only advisable, but very often essential.

#### Carbon Steel and Alloy Steel

These two groups of materials have, quite rightly, been given more attention in estimation of preheat temperature than any other alloy system, as the penalty for getting it wrong can be severe.

The following list is intended only to give some indication of the level of preheat required for certain types of steel. In these examples, it is assumed that the weld is a butt weld, and the thicknesses given are the normally used 'combined thickness', where this is the total thickness of all the parts to be joined.

When calculating the 'combined thickness' of parts with varying thicknesses (such as forgings), the thickness of each part is usually averaged over a distance of 75 mm from the weld line. However, for some processes and materials, account must be taken of any difference of thickness beyond the 75 mm point, and it is important to refer to the specific welding procedures or relevant standards in each case.



Steel Type	Combined Thickness (mm)	Typical Preheat (°C)
Low C and mild steels	<50	50
	>50	100 – 150
Medium C, CMn steels	<40	100 – 200
	>40	150 – 250
High C, CMn steels	All	200 – 300
QT steels, HSLA steels	All	None to 150 (max.)
0,5% Mo, 1% Cr-0,5% Mo steels*	All	100 – 250
2% Cr-1% Mo, 5% Cr-0,5% Mo steels*	All	200 – 300
Direct hardening steels	All	150 – 300
Case hardening steels	All	150
13% manganese steel	All	None

\*Preheat is usually specified by procedure and tightly monitored and controlled with these materials

It is recommended that more comprehensive documentation be consulted when selecting a temperature for a specific application.

Information to assist with calculation of preheat for CMn steels can be found in international standards (e.g. BS 5135 and AWS D1.1). These standards set out minimum preheat temperatures based on factors such as the type of steel specification or carbon equivalent, thickness, the welding process or heat input, and the hydrogen class of the welding consumable. The guidelines do not take restraint into consideration, so highly restrained joints may need higher levels of preheat than indicated.

The information in these standards is often used as a rough guide to determine preheat for low alloy steels. This should be done with extreme caution, as low alloy steels will frequently need much higher preheat than estimated by this means because of their alloy content.

When joining or surfacing hardenable steels (steels with high CE), it is sometimes possible to weld with an austenitic type consumable and to use a lower preheat than would be needed if ferritic consumables were to be used.

The decision-making process, when deciding whether to use preheat with carbon steel and alloy steel, can become quite complicated. Carbon and carbon-manganese steels and low alloy steels may require preheating, but this depends on their carbon equivalent, combined thickness and proposed welding heat input.

Preheat with these ferritic materials is primarily aimed at reducing the severity of the 'quench' after welding, and helping to prevent the formation of hard brittle microstructures in the weld and HAZ. It also allows hydrogen to diffuse away from the weld area, thus reducing the risk of hydrogen cracking. The objective is to keep the maximum HAZ hardness to below about 350 HV although this will not always be possible, particularly with some low alloy steels with high hardenability. These low alloy types may, additionally, need a post weld heat treatment to restore properties.

### How Much Preheat to Apply

The actual preheat temperature required for a specific welding operation depends not only on the material or materials being welded, but also the combined thickness of the joint, the heat input from the welding process being used, and the amount of restraint imposed upon the components. There are no hard and fast rules regarding how much preheat to apply, but there are many publications available that give helpful guidance.

## Fundamentals of Manual Metal Arc (MMA) Welding

### Welding Technique

Successful MMA welding depends on the following factors:

- Selection of the correct electrode
- Selection of the correct size of the electrode for the job
- Correct welding current
- Correct arc length
- Correct angle of electrode to work
- Correct travel speed
- Correct preparation of work to be welded.

### Electrode Selection

As a general rule, the selection of an electrode is straightforward, in that it is only a matter of selecting an electrode of similar composition to the parent metal. However, for some metals there is a choice of several electrodes, each of which has particular properties to suit specific classes of work. Often, one electrode in the group will be more suitable for general applications due to its all round qualities.

The table below shows just a few of the range of electrodes available from Afrox, with their typical areas of application.

For example, the average welder will carry out most fabrication using mild steel and for this material has a choice of various standard Afrox electrodes, each of which will have qualities suited to particular tasks. For general mild steel work, however, Afrox Vitemax® electrodes will handle virtually all applications. Afrox Vitemax® is suitable for welding mild steel in all positions using AC or DC power sources. Its easy striking characteristics and the tolerance it has for work where fit-up and plate surfaces are not considered good, make it the most attractive electrode of its class.

### Electrodes and Typical Applications

Name	AWS Classification	Application
Afrox Vitemax®	E6013	A premium quality electrode for general structural and sheet metal work in all positions, including vertical-down using low carbon steels
Afrox Afrolux	E7024	An iron powder electrode for high speed welding of H-V fillets and flat butt joints. Medium to heavy structural applications in low carbon steels

Name	AWS Classification	Application
Afrox 7018-1	E7018-1	A premium quality, all positional hydrogen-controlled electrode for carbon steels in pressure vessel applications and where high integrity welding is required; and for free-machining steels containing sulphur

### Electrode Size

The size of the electrode generally depends on the thickness of the section being welded, and the thicker the section the larger the electrode required. In the case of light sheet, the electrode size used is generally slightly larger than the work being welded. This means that, if 2,0 mm sheet is being welded, 2,5 mm diameter electrode is the recommended size.

The following table gives the maximum size of electrodes that may be used for various thicknesses of section.

### Recommended Electrode Sizes

Average Thickness of Plate or Section (mm)	Maximum Recommended Electrode Diameter (mm)
1,5 – 2,0	2,5
2,0 – 5,0	3,2
5,0 – 8,0	4,0
8,0	5,0

### Welding Current

Correct current selection for a particular job is an important factor in arc welding. With the current set too low, difficulty is experienced in striking and maintaining a stable arc. The electrode tends to stick to the work, penetration is poor and beads with a distinct rounded profile will be deposited.

Excessive current is accompanied by overheating of the electrode. It will cause undercut and burning through of the material, and will give excessive spatter. Normal current for a particular job may be considered as the maximum, which can be used without burning through the work, overheating the electrode or producing a rough spattered surface (i.e. the current in the middle of the range specified on the electrode package is considered to be the optimum).

In the case of welding machines with separate terminals for different size electrodes, ensure that the welding lead is connected to the correct terminal for the size electrode being used. When using machines with adjustable current, set on the current range specified. The limits of this range should not normally be exceeded. The following table shows the current ranges generally recommended for Vitemax®.

### Generally Recommended Current Range for Afrox Vitemax®

Electrode Size (mm)	Current Range (A)
2,5	60 – 95
3,2	110 – 130
4,0	140 – 165
5,0	170 – 260

### Arc Length

To strike the arc, the electrode should be gently scraped on the work until the arc is established. There is a simple rule for the proper arc length; it should be the shortest arc that gives a good surface to the weld. An arc too long reduces penetration, produces spatter and gives a rough surface finish to the weld. An excessively short arc will cause sticking of the electrode and rough deposits that are associated with slag inclusions.

For downhand welding, an arc length not greater than the diameter of the core wire will be most satisfactory. Overhead welding requires a very short arc, so that a minimum of metal will be lost. Certain Afrox electrodes have been specially designed for 'touch' welding. These electrodes may be dragged along the work and a perfectly sound weld is produced.

### Electrode Angle

The angle that the electrode makes with the work is important to ensure a smooth, even transfer of metal.

The recommended angles for use in the various welding positions are covered later.

### Correct Travel Speed

The electrode should be moved along in the direction of the joint being welded at a speed that will give the size of run required. At the same time, the electrode is fed downwards to keep the correct arc length at all times. As a guide for general applications, the table below gives recommended run lengths for the downhand position.

Correct travel speed for normal welding applications varies between approximately 100 and 300 mm per minute, depending on electrode size, size of run required and the amperage used.

Excessive travel speeds lead to poor fusion, lack of penetration, etc. while too slow a rate of travel will frequently lead to arc instability, slag inclusions and poor mechanical properties.

### Run Length per Electrode – Afrox

Electrode Size (mm)	Electrode Length (mm)	Run Length (mm)	
		Min	Max
4,0	350	175	300
3,2	350	125	225
2,5	350	100	225

### Correct Work Preparation

The method of preparation of components to be welded will depend on equipment available and relative costs. Methods may include sawing, punching, shearing, machining, flame cutting and others.

In all cases, edges should be prepared for the joints that suit the application. The following section describes the various joint types and areas of application.


### Types of Joints

#### Butt welds

A butt weld is a weld made between two plates so as to give continuity of section.

Close attention must be paid to detail in a butt weld to ensure that the maximum strength of the weld is developed. Failure to properly prepare the edges may lead to the production of faulty welds, as correct manipulation of the electrode is impeded.

#### Butt Welding

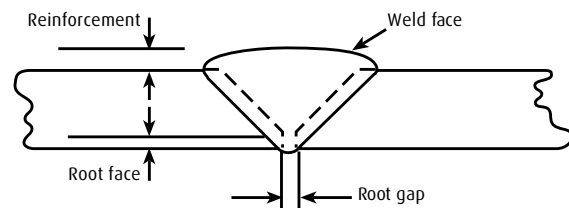

Two terms relating to the preparation of butt welds require explanation at this stage. They are:

- Root face: the proportion of the prepared edge that has not been bevelled (land)
- Root gap: the separation between root faces of the parts to be joined.

Various types of butt welds are in common use and their suitability for different thickness of steel are described as follows:

#### Square Butt Weld



The edges are not prepared, but are separated slightly to allow fusion through the full thickness of the steel. Suitable for plate up to 6 mm in thickness

#### Single 'V' Butt Weld




This is commonly used for plate up to 16 mm in thickness and on metal of greater thickness where access is available from only one side

#### Double 'V' Butt Weld



Used on plate of 12 mm and over in thickness when welding can be applied from both sides. It allows faster welding and greater economy of electrodes than a single 'V' preparation on the same thickness of steel and also has less tendency to distortion as weld contraction can be equalised

#### Butt Weld with Backing Material



When square butt welds or single 'V' welds cannot be welded from both sides, it is desirable to use a backing bar to ensure complete fusion

### Single 'U' Butt Weld



Used on thick plates as an alternative to a single 'V' preparation. It has advantages in speed of welding. It takes less weld metal than a single 'V', there is less contraction and there is, therefore, a lessened tendency to distortion. Preparation is more expensive than in the case of a 'V', as machining is required. This type of joint is most suitable for material over 40 mm in thickness.

### Double 'U' Butt Weld



For use on thick plate that is accessible for welding from both sides. For a given thickness it is faster, needs less weld metal and causes less distortion than a single 'U' preparation.

### Horizontal Butt Weld



The lower member in this case is bevelled to approximately 15° and the upper member 45°, making an included angle of 60°. This preparation provides a ledge on the lower member, which tends to retain the molten metal.

### General notes on butt welds

The first run in a prepared butt weld should be deposited with an electrode not larger than 4,0 mm. The angle of the electrode for the various runs in a butt weld is shown opposite.

It is necessary to maintain the root gap by tacking at intervals or by other means, as it will tend to close during welding.

All single 'V', single 'U' and square butt welds should have a backing run deposited on the underside of the joint, otherwise 50% may be deducted from the permissible working stress of the joint.


Before proceeding with a run on the underside of a weld, it is necessary to back-gouge or grind that side of the joint.

Butt welds should be overfilled to a certain extent by building up the weld until it is above the surface of the plate. Excessive reinforcement, however, should be avoided.


In multi-run butt welds, it is necessary to remove all slag and surplus weld metal before a start is made on additional runs. This is particularly important with the first run, which tends to form sharp corners that cannot be penetrated with subsequent runs. Electrodes larger than 4,0 mm are not generally used for vertical or overhead butt welds.

The diagrams opposite indicate the correct procedure for welding thick plate when using multiple runs.


### Bead Sequence for 1st and 2nd Layers

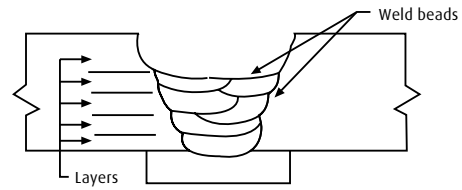

### Bead Sequence for Subsequent Layers

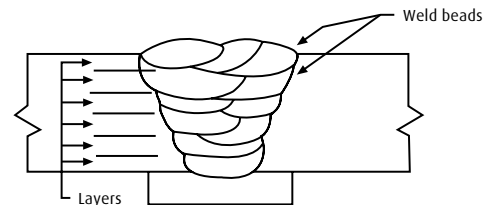

### Welding Progression Angle

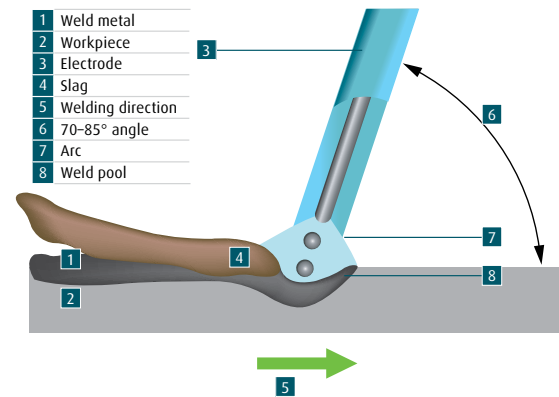


### Fillet welds

A fillet weld is approximately triangular in section, joining two surfaces not in the same plane and forming a lap joint, 'T' joint or corner joint. Joints made with fillet welds do not require extensive edge preparation, as is the case with butt welded joints, since the weld does not necessarily penetrate the full thickness of either member. It is, however, important that the parts to be joined be clean, close fitting, and that all the edges on which welding is to be carried out are square. On sheared plate, it is advisable to entirely remove any 'false cut' on the edges prior to welding.


Fillet welds are used in the following types of joints:

### 'T' Joints

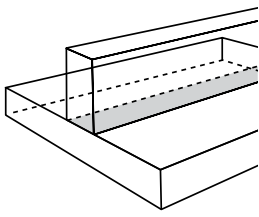


A fillet weld may be placed either on one or both sides, depending on the requirements of the work. The weld metal should fuse into or penetrate the corner formed between the two members. Where possible, the joint should be placed in such a position as to form a 'natural V' fillet since this is the easiest and fastest method of fillet welding

### Lap Joints

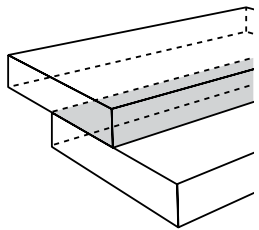

In this case, a fillet weld may be placed either on one or both sides of the joint, depending on accessibility and the requirements of the joint. However, lap joints, where only one weld is accessible, should be avoided where possible and must never constitute the joints of tanks or other fabrications where corrosion is likely to occur behind the lapped plates. In applying fillet welds to lapped joints, it is important that the amount of overlap of the plates be not less than five times the thickness of the thinner part. Where it is required to preserve the outside face or contour of a structure, one plate may be joggled

### Corner Joints

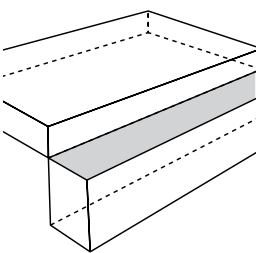

The members are fitted as shown, leaving a 'V'-shaped groove in which a fillet weld is deposited. Fusion should be complete for the full thickness of the metal. In practice, it is generally necessary to have a gap or a slight overlap on the corner. The use of a 1,0–2,5 mm gap has the advantage of assisting penetration at the root, although setting up is a problem. The provision of an overlap largely overcomes the problem of setting up, but prevents complete penetration at the root and should therefore be kept to a minimum (i.e. 1,0–2,5 mm)

The following terms and definitions are important in specifying and describing fillet welds.

### Leg length

A fusion face of a fillet weld, as shown on the right.

### Throat thickness


A measurement taken through the centre of a weld from the root to the face, along the line that bisects the angle formed by the members to be joined. Many countries use throat thickness rather than leg length.

Effective throat thickness is a measurement on which the strength of a weld is calculated. The effective throat thickness is based on a mitre fillet (concave fillet weld), which has a throat thickness equal to 70% of the leg length. For example, in the case of a 20 mm fillet, the effective throat thickness will be 14 mm.

### Convex fillet weld

A fillet weld in which the contour of the weld metal lies outside a straight line joining the toes of the weld. A convex fillet weld of specified leg length has a throat thickness in excess of the effective measurement.


#### Convex Fillet Weld

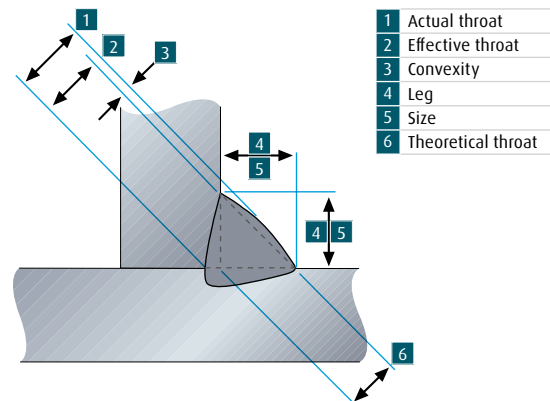

### Concave fillet weld

A fillet in which the contour of the weld is below a straight line joining the toes of the weld. It should be noted that a concave fillet weld of a specified leg length has a throat thickness less than the effective throat thickness for that size fillet. This means that, when a concave fillet weld is used, the throat thickness must not be less than the effective measurement. This entails an increase in leg length beyond the specified measurement

#### Concave Fillet Weld

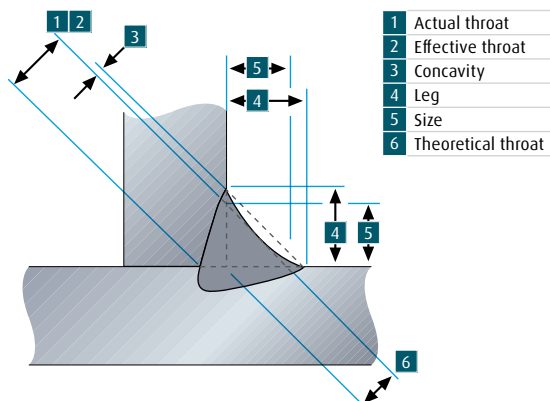

The size of a fillet weld is affected by the electrode size, welding speed or run length, welding current and electrode angle. Welding speed and run length have an important effect on the size and shape of the fillet, and on the tendency to undercut.


Insufficient speed causes the molten metal to pile up behind the arc and eventually to collapse. Conversely, excessive speed will produce a narrow irregular run having poor penetration, and where larger electrodes and high currents are used, undercut is likely to occur.

**Fillet weld data**

Nominal Fillet Size (mm)	Min. Throat Thickness (mm)	Plate Thickness (mm)	Electrode Size (mm)
5,0	3,5	5,0 – 6,3	3,2
6,3	4,5	6,3 – 12,0	4,0
8,0	5,5	8,0 – 12,0 and over	5,0
10,0	7,0	10,0 and over	4,0

Selection of welding current is important. If it is too high, the weld surface will be flattened and undercut accompanied by excessive spatter is likely to occur. Alternatively, a current which is too low will produce a rounded narrow bead with poor penetration at the root. The first run in the corner of a joint requires a suitably high current to achieve maximum penetration at the root. A short arc length is recommended for fillet welding. The maximum size fillet which should be attempted with one pass of a large electrode is 8,0 mm. Efforts to obtain larger leg lengths usually result in collapse of the metal at the vertical plate and serious undercutting. For large leg lengths, multiple run fillets are necessary. These are built up as shown below. The angle of the electrode for various runs in a downhand fillet weld is also shown.

**Recommended electrode angles for fillet welds**

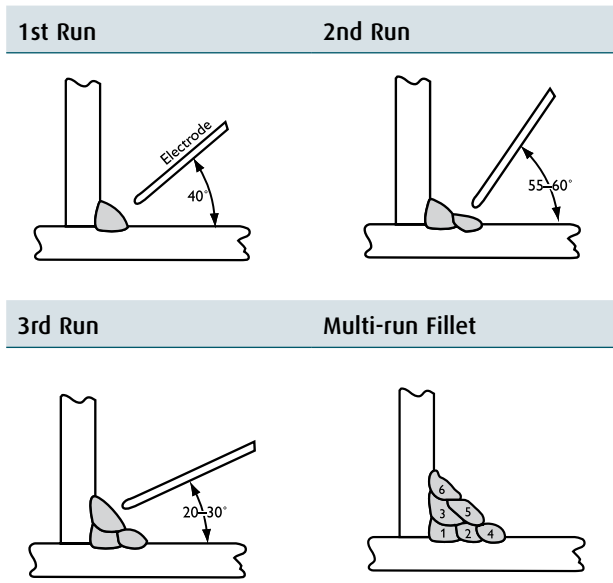

Multi-run (multi-pass) horizontal fillets have each run made using the same run lengths (Run Length per Electrode table). Each run is made in the same direction, and care should be taken with the shape of each, so that it has equal leg lengths and the contour of the completed fillet weld is slightly convex with no hollows in the face.


Vertical fillet welds can be carried out using the upwards or downwards technique. The characteristics of each are: Upwards – current used is low, penetration is good, surface is slightly convex and irregular. For multiple run fillets, large single-pass weaving runs can be used. Downwards – current used is medium, penetration is poor, each run is small, concave and smooth.

The downwards method should be used for making welds on thin material only. Electrodes larger than 4,0 mm are not recommended for vertical-down welding. All strength joints in vertical plates 10,0 mm thick or more should be welded using the upward technique. This method is used because of its good penetration and weld metal quality. The first run of a vertical-up fillet weld should be a straight sealing run made with 3,2 mm or 4,0 mm diameter electrode. Subsequent runs for large fillets may be either numerous straight runs or several wide weaving runs.

Correct selection of electrodes is important for vertical welding.

In overhead fillet welds, careful attention to technique is necessary to obtain a sound weld of good profile. Medium current is required for best results. High current will cause undercutting and bad shape of the weld, while low current will cause slag inclusions. To produce a weld having good penetration and of good profile, a short arc length is necessary. Angles of electrode for overhead fillets is illustrated below.

**Recommended Electrode Angles for Overhead Fillet Welds**

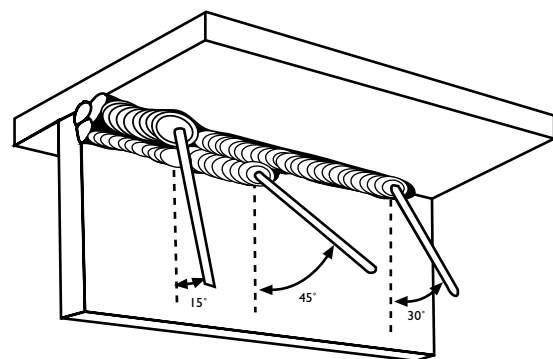

## Welding Defects and Problems

Manual metal arc welding, like other welding processes, has welding procedure problems that may develop and which can cause defects in the weld. Some defects are caused by problems with the materials. Other welding problems may not be foreseeable and may require immediate corrective action. A poor welding technique and improper choice of welding parameters can cause weld defects.

Defects that can occur when using the shielded metal arc welding process are slag inclusions, wagon tracks, porosity, wormhole porosity, undercutting, lack of fusion, overlapping, burn through, arc strikes, craters and excessive weld spatter. Many of these welding technique problems weaken the weld and can cause cracking. Other problems that can occur and which can reduce the quality of the weld are arc blow, finger nailing and improper electrode coating moisture contents.

### Defects Caused by Welding Technique

#### Slag inclusions




Slag inclusions occur when slag particles are trapped inside the weld metal, which produces a weaker weld. These can be caused by:

- Erratic travel speed
- Too wide a weaving motion
- Slag left on the previous weld pass
- Too large an electrode being used
- Letting slag run ahead of the arc.

This defect can be prevented by:

- A uniform travel speed
- A tighter weaving motion
- Complete slag removal before welding
- Using a smaller electrode
- Keeping the slag behind the arc, which is done by shortening the arc, increasing the travel speed or changing the electrode angle.


#### Wagon tracks

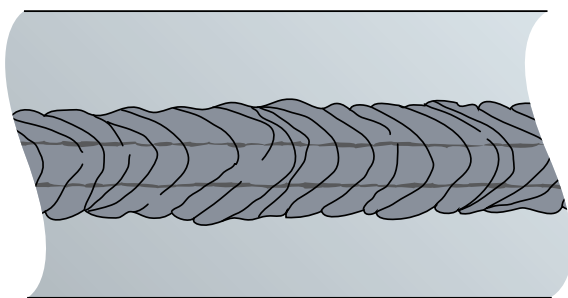

Top view through transparent bead

Wagon tracks are linear slag inclusions that run the longitudinal axis of the weld. They result from allowing the slag to run ahead of the weld puddle and by slag left on the previous weld pass. These occur at the toe lines of the previous weld bead.

#### Porosity



Porosity is gas pockets in the weld metal that may be scattered in small clusters or along the entire length of the weld. Porosity weakens the weld in approximately the same way that slag inclusions do.


Porosity may be caused by:

- Excessive welding current
- Rust, grease, oil or dirt on the surface of the base metal
- Excessive moisture in the electrode coatings
- Impurities in the base metal
- Too short an arc length, except when using low hydrogen or stainless steel electrodes
- Travel speed too high, which causes freezing of the weld puddle before gases can escape.

This problem can be prevented by:

- Lowering the welding current
- Cleaning the surface of the base metal
- Re-drying electrodes
- Changing to a different base metal with a different composition
- Using a slightly longer arc length
- Lowering the travel speed to let the gases escape
- Preheating the base metal, using a different type of electrode, or both.

#### Wormhole porosity (Piping porosity)

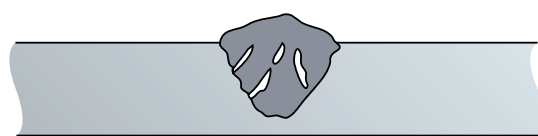

Wormhole porosity is the name given to elongated gas pockets. The best method of preventing this is to lower the travel speed to permit gases to escape before the weld metal freezes.

#### Undercutting



Undercutting is a groove melted in the base metal next to the toe or root of a weld that is not filled by the weld metal. Undercutting causes a weaker joint and it can cause cracking. This defect is caused by:

- Excessive welding current
- Too long an arc length

- Excessive weaving speed
- Excessive travel speed.

On vertical and horizontal welds, it can also be caused by too large an electrode size and incorrect electrode angles. This defect can be prevented by:

- Choosing the proper welding current for the type and size of electrode and the welding position
- Holding the arc as short as possible
- Pausing at each side of the weld bead when a weaving technique is used
- Using a travel speed slow enough so that the weld metal can completely fill all of the melted out areas of the base metal.

### Lack of fusion




Lack of fusion is when the weld metal is not fused to the base metal. This can occur between the weld metal and the base metal or between passes in a multiple-pass weld. Causes of this defect can be:

- Excessive travel speed
- Electrode size too large
- Welding current too low
- Poor joint preparation
- Letting the weld metal get ahead of the arc.

Lack of fusion can usually be prevented by:

- Reducing the travel speed
- Using a smaller diameter electrode
- Increasing the welding current
- Better joint preparation
- Using a proper electrode angle.

### Overlapping



Overlapping is the protrusion of the weld metal over the edge or toe of the weld bead. This defect can cause an area of lack of fusion and create a notch, which can lead to crack initiation. Overlapping is often produced by:

- Too slow a travel speed, which permits the weld puddle to get ahead of the electrode
- An incorrect electrode angle.

### Legend to Welding Position Abbreviations

Symbol	Abbreviation	Description
	F	Flat
	H-V FILLET	Horizontal-Vertical Fillet
	H	Horizontal
	V	Vertical
	V-DOWN	Vertical-Down
	OH	Overhead

### Coating Types

It is the composition of the coating that differentiates one type of electrode from another and, to a degree, what type of application it can be used for. MMA electrodes, with a solid wire core, are generally categorised by the type of flux coating they employ. There are three main groups of electrode coating: rutile, basic and cellulosic, plus a less widely used acid type. The name of each group is a description of the main constituent of the coating. Although not strictly a coating type, iron powder electrodes are often considered as a separate group.

Electrodes for cutting, grooving and gouging, plus those for hard surfacing, including tubular MMA electrodes, are not classified by coating type.

#### Rutile Electrodes

Rutile electrodes have a coating that contains about 50% rutile sand (a pure form of titanium dioxide), plus additions of ferro-manganese, mineral carbonates and silicates, held together with approximately 15% sodium silicate, also known as waterglass. The rutile's characteristics include easy striking, stable arc, low spatter, good bead profile and, generally, easy slag removal from the electrode.

The electrode can operate on both AC and DC currents and can operate in all positions if the formulation of the coating is so designed.

One negative aspect of these electrodes is that they produce a high level of hydrogen, typically greater than 15 ml/100 g of deposited weld metal. This cannot be avoided, because they rely on a certain amount of moisture being present in the coating to operate properly. If the electrodes are dried too much, they will fail to function properly.

Rutile coated electrodes are manufactured for welding mild and low carbon steels. In this context, they are often referred to as general purpose or GP electrodes. Some low alloy grades also use rutile coatings. Rutile type coatings, which are modifications of those used for ferritic steels, are also used on many austenitic stainless steel electrodes.



### Basic Electrodes

Basic, or low hydrogen electrodes contain calcium carbonate and calcium fluoride in place of the rutile sand and mineral silicates. This makes them less easy to strike and more difficult to re-strike, due to the very deep cup formed at the tip during operation. They also have a poorer, more convex bead profile than rutile electrodes. The slag is more difficult to remove than the rutile types, but they do give better weld metal properties than rutile types, with a higher metallurgical quality.

Basic electrodes are capable of being used on AC or DC currents and can be used in multi-pass welds on materials of all thicknesses.

Basic electrodes do not rely on moisture to function properly, and for the more critical applications should be used completely dry. It is important to note that basic electrodes are only low hydrogen electrodes if they have been correctly dried before use. This conventionally involves re-drying in ovens on site in accordance with manufacturers' recommendations. Drying can reduce weld metal hydrogen to less than 5 ml/100 g, as can vacuum-packing the electrodes.

### Cellulosic Electrodes

Cellulosic electrodes contain a high proportion of organic material, replacing all or some of the rutile sand. This produces a fierce, deep penetrating arc and a faster burn-off rate. Cellulosic electrodes are more prone to spatter than rutile types. Only carbon and some low alloy steels are made with a cellulosic coating and most run only on DC+ polarity, but some are made that will also operate on AC and DC-. They are truly all-positional electrodes in all sizes and even larger diameters up to 6 mm will operate vertical-down. Cellulosic electrodes are used for root passes and pipeline welding.

It should be noted that cellulosic electrodes generate high amounts of hydrogen. This presents a risk of hydrogen-induced cracking if correct welding procedures are not followed.

### Acid Electrodes

Acid electrodes for mild steels have been largely replaced by rutile types, but some are still produced by a few manufacturers. These electrodes contain high amounts of iron oxide, are relatively easy to use and give a voluminous glassy slag that detaches easily. They are lower-strength products, so they are confined to use on non-structural components.

Acid-rutile electrodes for stainless steel are now replacing conventional rutile types. They are higher in silicon, which gives improved operating and wetting characteristics, and they are much more welder-friendly. They strike and re-strike readily and will operate on AC and DC current. They produce low spatter levels and an easily removed slag. However, they are prone to 'start porosity' and need re-drying before use to avoid this.

### Iron Powder Electrodes

Iron powder electrodes are often considered an independent group of consumables. As their name suggests, these electrodes contain high levels of iron powder held within the coating – as the coating melts, the iron powder creates more weld metal. This effectively improves the productivity from the electrode, allowing either larger or longer welds to be created from a single rod. The amount of iron powder added depends on the consumable being produced, but it is not uncommon for 75% of the core weight to be added.

The addition of the iron powder to the coating has the effect of increasing the overall diameter of the electrode and reducing the amount of fluxing agent present in the coating. With less fluxing agent available, the slag coating tends to be thinner, so many of the MMA electrode's positional welding characteristics are lost. This means that many of the electrodes can only be used in the flat or horizontal-vertical (H-V) positions.

Coatings for iron powder electrodes may be based on either the rutile or basic systems.

## Fundamentals of Metal Inert Gas (MIG) Welding

### Welding Technique

Successful welding depends on the following factors:

- Selection of correct consumables
- Selection of the correct power source
- Selection of the correct shielding gas
- Selection of the correct application techniques:
  - Correct angle of electrode to work
  - Correct electrical stick out
  - Correct travel speed
- Selection of the welding preparation.

### Selection of Correct Consumables

#### Chemical composition

As a general rule, the selection of a wire is straightforward, in that it is only a matter of selecting an electrode of similar composition to the parent material. However, there are certain applications for which electrodes will be selected on the basis of mechanical properties or the level of residual hydrogen in the weld metal. Solid MIG wires are all considered to be of the 'low hydrogen type' consumables.

#### Physical condition


##### Surface condition

The welding wire must be free from any surface contamination, including mechanical damage such as scratch marks.

A simple test for checking the surface condition is to run the wire through a cloth that has been dampened with acetone for 20 seconds. If a black residue is found on the cloth, the surface of the wire is not properly cleaned.

##### Cast and helix

The cast and helix of the wire has a major influence on the feedability of MIG wire.

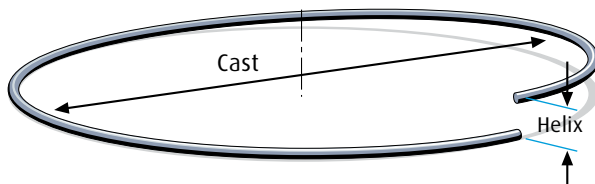

Cast – Diameter of the circle

Helix – Vertical height

If the cast is too small, the wire will dip down from the tip. The result of this is excessive tip wear and increased wear in the liners.

If the helix is too large, the wire will leave the tip with a corkscrew effect and cause feeding problems.

### Selection of the Correct Power Source

Power sources for MIG/MAG welding are selected on a number of different criteria, including:

- Maximum output of the machine
- Duty cycle
- Output control (voltage selection, wire feed speed control)
- Portability.

The following table and diagram gives an indication of the operating amperage for different size wires.


Wire Size (mm)	Amperage Range (A)
0,8	60 – 180
0,9	70 – 250
1,0	90 – 280
1,2	120 – 340

### Selection of the Correct Shielding Gas

The selection of the shielding gas has a direct influence on the appearance and quality of the weldbead.

The type and thickness of the material to be welded will determine the type of shielding gas that is selected. As a general rule, the thicker the material (CMn and alloy steels), the higher the percentage of CO<sub>2</sub> in the shielding gas mixture.


Wire Operating Limits

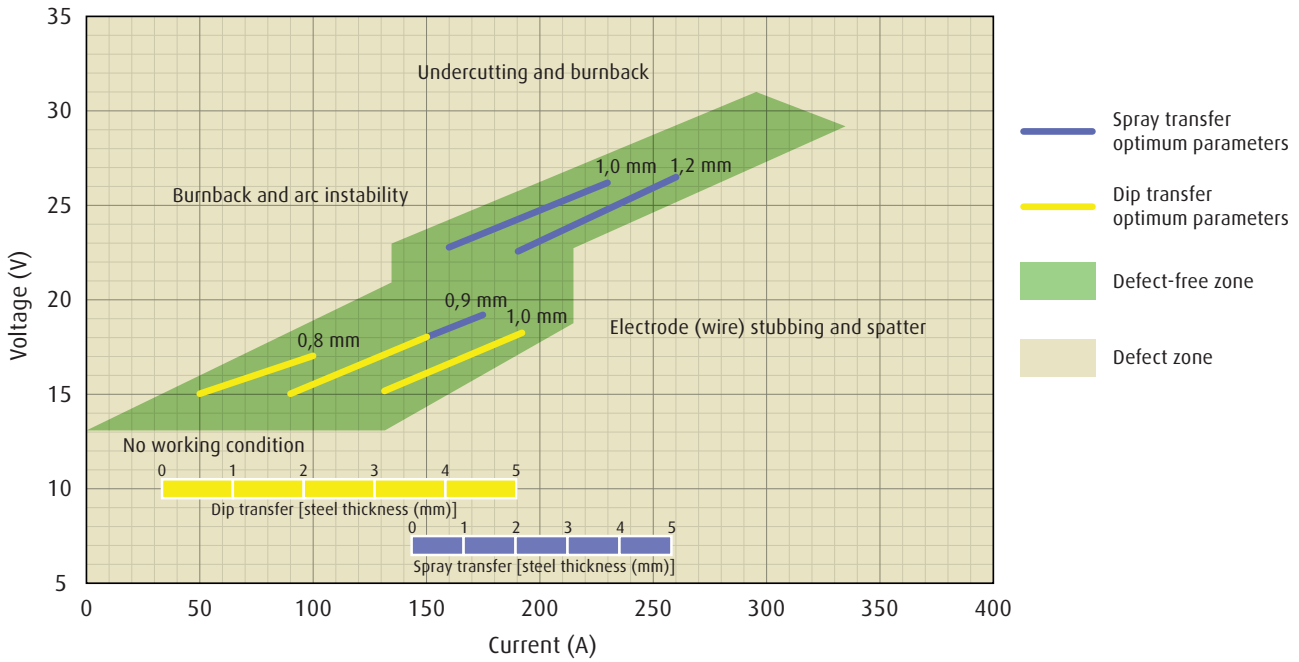


Correct Application Techniques

Direction of welding


MIG welding with solid wires takes place normally with a push technique. The welding gun is tilted at an angle of 10° towards the direction of welding (push technique).

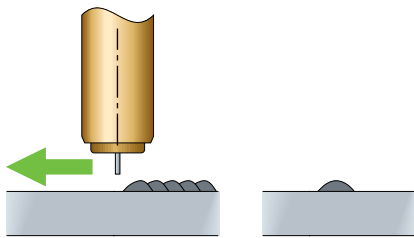


The influence of changing the torch angle and the welding direction on the weld bead profile can be seen below.

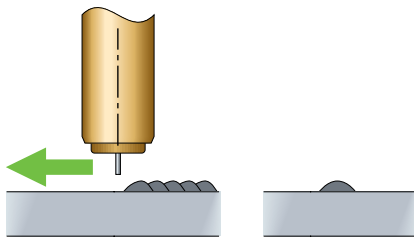

Torch perpendicular to workpiece. Narrow bead width with increased reinforcement.

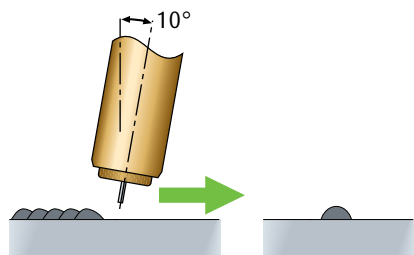


Torch positioned at a drag angle of 10°. Narrow bead width with excessive reinforcement.

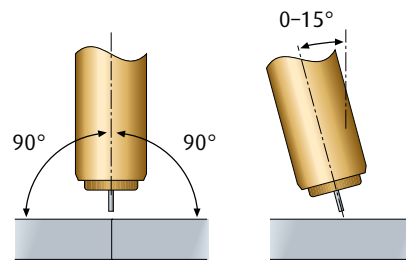

Torch position for butt welds


When welding butt welds, the torch should be positioned within the centre of the groove and tilted at an angle of ±15° from the vertical plane. Welding is still performed in the push technique.

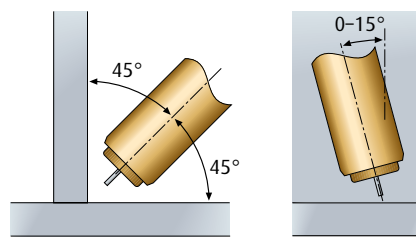


Torch position for fillet welds

When welding fillet welds, the torch should be positioned at an angle of 45° from the bottom plate, with the wire pointing into the fillet corner. Welding is still performed in the push technique.

### Electrical stick out

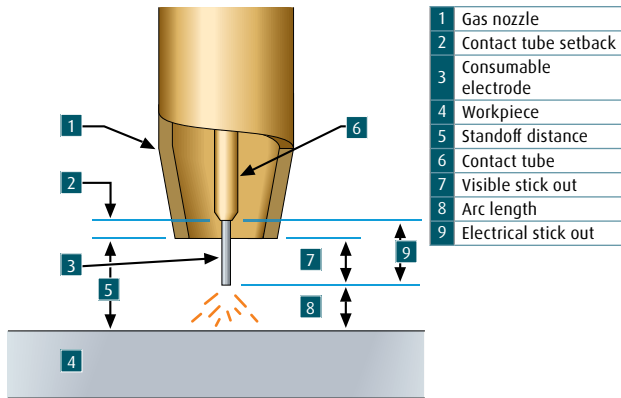


The electrical stick out is the distance between the end of the contact tip and the end of the wire. An increase in the electrical stick out results in an increase in the electrical resistance. The resultant increase in temperature has a positive influence in the melt-off rate of the wire that will have an influence on the weldbead profile.

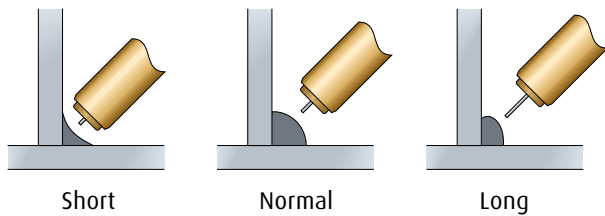

Influence of the change in electrical stick out length on the weldbead profile.

### Travel speed



The travel speed will influence the weldbead profile and the reinforcement height.

If the travel speed is too slow, a wide weldbead with excessive rollover will result. Conversely, if the travel speed is too high, a narrow weldbead with excessive reinforcement will result.

## Fundamentals of Flux and Metal Cored Arc Welding

### Welding Technique

Successful flux and metal cored arc welding depends on the following factors:

- Selection of correct consumables
- Selection of the correct power source
- Selection of the correct shielding gas
- Selection of the correct application techniques:
  - Correct angle of electrode to work
  - Correct electrical stick out
  - Correct travel speed
- Selection of the welding preparation.

### Selection of Correct Consumables

#### Chemical composition

As a general rule, the selection of a wire is straightforward, in that it is only a matter of selecting an electrode of similar composition to the parent material. However, there are certain applications for which electrodes will be selected on the basis of mechanical properties or the level of residual hydrogen in the weld metal. The classification system for flux cored wires will provide an indication of the residual hydrogen level that can be expected in the weldmetal.

#### Physical condition

The wire must be free from any surface contamination, including surface rust. Most flux and metal cored wires have a thin film of graphite on the surface of the wire to assist with feedability.

The AWS standard for flux cored wires does not specify a cast or helix, other than to stipulate that it should be of such a nature that the wire can be fed uninterrupted.

### Selection of the Correct Power Source

Power sources for flux and metal cored welding are selected on a number of different criteria, including:

- Maximum output of the machine
- Duty cycle
- Output control (voltage selection, wire feed speed control)
- Portability.

The following table gives an indication of the operating amperage for different size wires.


Wire Size (mm)	Direction	Amperage Range (A)
<b>FCAW</b>		
1,2	Horizontal	200 – 300
1,2	Vertical-up	150 – 250
1,6	Horizontal	300 – 400
1,6	Vertical-up	180 – 250
<b>MCAW</b>		
1,2	Horizontal	150 – 350
1,6	Horizontal	300 – 500

### Selection of the Correct Shielding Gas

The selection of the shielding gas has a direct influence on the appearance and quality of the weldbead.

Flux cored wires are manufactured to be welded with either 100% CO<sub>2</sub> or an argon-CO<sub>2</sub> gas mixture.

Current/Voltage Envelope for Argoshield® 52

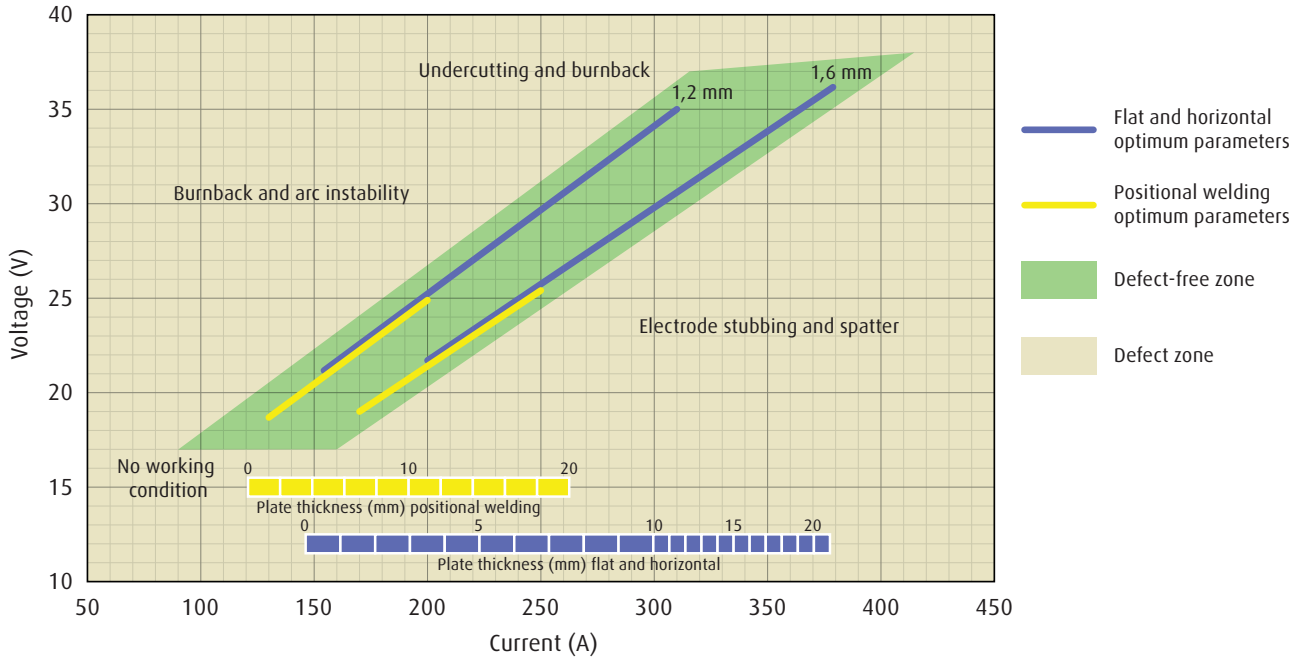


**Correct Application Techniques**

**Direction of travel**


Flux cored welding is normally performed using a 'drag' technique. The welding gun is tilted to a 50–60° backhand angle. If, however, a flatter bead profile is required, the backhand angle can be reduced.

Metal cored wire, because of its similarity to solid wires (no slag formers added to the core mainly metallic powders), are normally welded with the 'push' technique.

**Travel direction (Flux cored)**

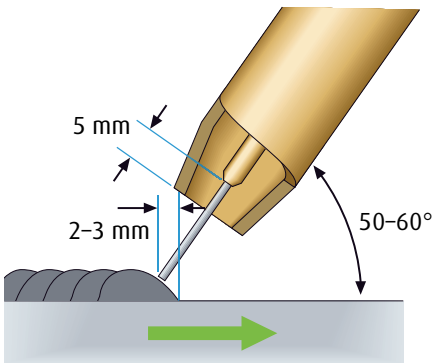


**Travel direction (Metal cored)**

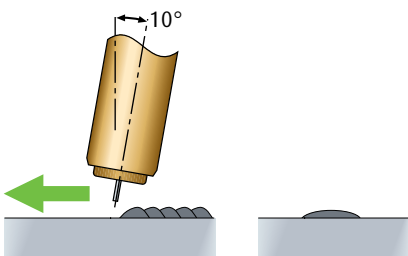


When welding butt welds with flux or metal cored wires, the torch should be positioned within the centre of the groove and tilted at an angle of ±20°. Flux cored welding is still performed with the 'drag' technique and metal cored welding with the 'push' technique.

**Torch position for butt welds**

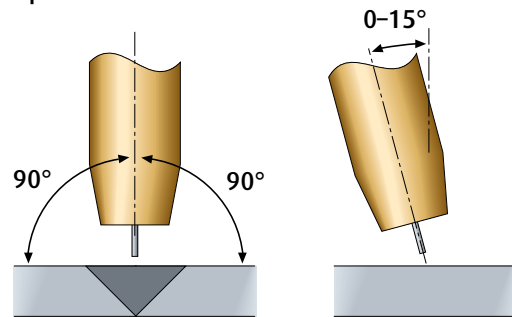

**Torch angle for fillet welds**

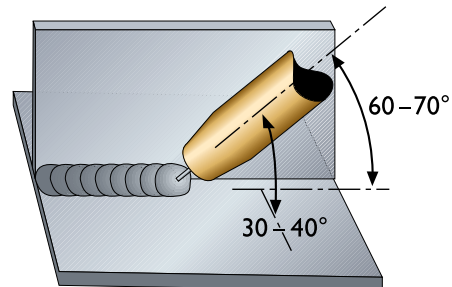


When welding horizontal-vertical fillet welds, the wire tip must be aimed exactly in the corner of the joint. For the first bead, the welding gun is tilted at an angle of 30–40° from the horizontal plane. Flux cored welding is still performed with the 'drag' technique and metal cored welding with the 'push' technique.

**Vertical-up**

Vertical-up welding can be undertaken in a similar way, as MMA with a slight weave motion. Vertical-up welding with metal cored wire can successfully be undertaken with pulsed MIG welding equipment.

**Electrical stick out**

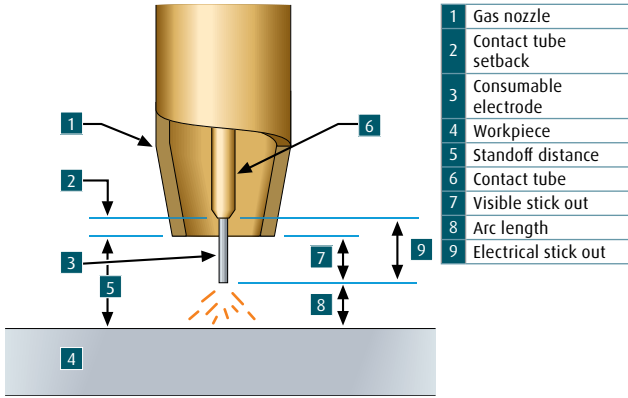

The electrical stick out is the distance between the end of the contact tip and the end of the wire. An increase in the electrical stick out results in an increase in the electrical resistance. The resultant increase in temperature has a positive influence in the melt-off rate of the wire that will have an influence on the weldbead profile.

**Travel speed**

The construction of flux and metal cored wires ensures the highest current density for a given current setting compared to all other welding processes.

High current densities produce high deposition rates.


$$\text{Current Density} = \frac{\text{Amperage}}{\text{Cross-sectional area of wire}}$$

$$\text{or } J = \frac{I}{A}$$

Electrode / Wire	Diameter (mm)	Cross Section Area (mm <sup>2</sup> )	Current (A)	Current Density (A/mm <sup>2</sup> )	Deposition Rate (kg/h)
MMA electrode (E7024)	4,0	12,57	235	18,7	3,0
FCAW wire (E71T-1)	1,2	0,625	235	376,0	3,8
MIG wire (ER70S-6)	1,2	1,130	235	287,5	3,3
MCAW wire (E70C-6M)	1,2	0,625	300	480,0	5,2


Consequently, travel speed must be increased proportionately to maintain control of the weld pool and bead shape, and to balance the deposited weld metal versus fusion obtained.

**Travel speed too slow**




Excessive penetration  
Excessive weld metal deposited  
Roll over of weld metal on horizontal plate

**Correct travel speed**



Recommended penetration depth  
Proper sidewall fusion without roll over or undercut

**Travel speed too fast**



Weld bead too small  
Inadequate sidewall fusion  
Lack of root penetration

# MMA Electrodes

## Vitemax®



Vitemax® is a premium quality rutile electrode for use in all positions including vertical downwards. The electrode has a smooth, quiet arc action, low spatter loss with good striking and restrike characteristics and excellent slag detachability. In most cases the slag is self-lifting. The electrode welds relatively cold which makes it ideally suited for bridging large gaps, i.e. where poor fit-up occurs and for tacking. This versatile electrode, which has a rapid burn-off rate, produces smooth welds in all positions. The weld metal deposited complies with radiographic quality to AWS A5.1 grade 1.

### Applications

Vitemax® is recommended for welding a wide variety of carbon- manganese steels having a carbon equivalent below 0,28%. It can also be used successfully in applications with higher carbon equivalents, provided the correct degree of preheat is used.

### Technique

Either the touch or free arc technique can be used. For vertical-down welding, the touch weld technique must be used with a high rate of travel.

### Re-drying Procedure

Rutile coated electrodes do not normally require re-drying prior to use, however if suspected of being damp, as shown by an erratic arc behaviour, the electrodes should be re-dried at 100-120°C for 1-2 hours.

### Classifications

AWS	A5.1	E6013
SABS	455	E4313/0315
EN	2560	E 38 0 RC 11

### Approvals

- Lloyds Register of Shipping Grade DXVu0,BF,2m,NR
- American Bureau of Shipping Grade 2
- Germanischer Lloyd Grade 2
- South African Bureau of Standards
- Det Norske Veritas (DNV)

### Typical Chemical Analysis (All weld metal)

% Carbon	0,05 - 0,1	% Sulphur	0,025 max
% Manganese	0,35 - 0,6	% Phosphorous	0,025 max
% Silicon	0,2 - 0,5		

### Typical Mechanical Properties (All weld metal in the as welded condition)

Yield Strength	400 MPa min
Tensile Strength	460 - 530 MPa
% Elongation on 50 mm	24 min
Charpy V-Notch at +20°C	70 J min
Charpy V-Notch at 0°C	50 J min



### Typical Current Values (AC 50 OCV min or DC+/-)

Diameter (mm)	Current (A)
2,0	40 - 80
2,5	60 - 95
3,15	110 - 130
4,0	140 - 165
5,0	170 - 260
6,3	270 - 340

### Deposition Data

Note:

- 1) The deposition data given was established at the optimum current rating which would be approximately in the middle of the specified range.
- 2) The mass of weld metal deposited per arc hour is a theoretical value which does not take into account welder efficiency.

Diameter (mm)	Mass of an Electrode (g)	Burn-off Time (sec)	Mass of Metal Deposited per Electrode (g)	Mass of Weld Metal Deposited per Arc Hour (g)	No. Electrodes per kg of Weld Metal	kg Weld Metal per kg of Electrodes
2,0	11,2	54,2	5,6	371	180	0,49
2,5	19,9	68,0	11,1	552	91	0,55
3,15	29,7	72,2	17,6	931	57	0,59
4,0	48,7	86,7	28,2	1 172	36	0,58
5,0	87,9	120,2	56,9	1 703	18	0,64
6,3	138,1	138,5	88,7	2 306	12	0,64

### Data for Welding Horizontal Fillet Welds

Diameter (mm)	Throat Thickness (mm)	Current (A)	Arc Time (sec)	Bead Length per Electrode (mm)	Welding Speed (m/hr)
2,0	1,5	65	39,5	139	12,7
2,5	2,8	85	55,1	198	13,6
3,15	3,5	125	61,1	202	11,9
4,0	4,0	165	69,0	207	10,8
5,0	5,0	230	105,7	313	10,7
6,3	5,3	320	139,7	374	9,6

### Packing Data

Diameter (mm)	Electrode Length (mm)	Item Number (1 kg pack)	Item Number (multi-kg pack)	Pack Mass (kg)	Approx. No. Electrodes/kg
2,0	300	W072001	W075001	3 x 4,0	89
2,5	350	W072002	W075002	3 x 5,0	50
3,15	350	W072003	W075003	3 x 5,0	34
4,0	350	W072004	W075004	3 x 5,0	21
5,0	450	-	W075005	3 x 6,0	11
6,3	450	-	W075007	3 x 6,0	7

## ARCMate 6013



ARCMate 6013 is a standard general purpose rutile type electrode for welding mild steels in all positions using AC/DC power source. The electrode performs exceptionally when compared to other equivalent product and displays good properties such as good striking, arc stability, low spatter, easy re-striking and slag removal.

### Applications

For general DIY welding of mild steels.

Classifications		
AWS	A5.1	E6013
SABS	2560	E350 RC 11
EN ISO	2560	E350 RC 11

Chemical Composition (Typical)					
% Carbon	0,06	% Sulphur	<0,02	% Chromium	0,05
% Manganese	0,40	% Phosphorous	0,013	% Molybdenum	0,01
% Silicon	0,25	% Nickel	0,02	% Vanadium	0,02

Typical Mechanical Properties (All weld metal in the as welded condition)	
Yield Strength	>400 MPa
Tensile Strength	>500 MPa
% Elongation on 50 mm	>25
Charpy V-Notch at +20°C	>70 J
Charpy V-Notch at 0°C	>40 J

Typical Current Values (AC 50 OCV min or DC+/-)	
Diameter (mm)	Current (A)
2,5	60 - 85
3,15	110 - 130
4,0	140 - 165

Packing Data			
Diameter (mm)	Electrode Length (mm)	Item Number	Pack Mass (kg)
2,5	350	W075152	5,0
3,15	350	W075153	5,0
4,0	350	W075154	5,0

## Transarc® 6013



Transarc® 6013 is a newly developed electrode from Afrox, produced locally at the world class manufacturing facility in Brits. The Brits consumables factory adopts the best manufacturing practices and standards and undergoes regular audits from approval bodies such as TÜV and SABS, ensuring that quality is not compromised and the highest standards are maintained on all the products.

Transarc® 6013 is a rutile electrode of a very good quality for welding mild steels. Transarc® 6013 has been developed and produced with a brand new formulation after extensive research.

### Applications

Suitable electrode for mild steel welding, fillet, tack and butt welding, and for bridging large joint gaps and welding that requires a smooth and clean bead appearance.

#### Classifications

AWS	A5.1	E6013
SANS	2560	E 350 RC 11
EN ISO	2560	E 350 RC 11

#### Typical Chemical Analysis (All weld metal)

% Carbon	0,04 - 0,055	% Molybdenum	0,002
% Manganese	0,5 - 0,6	% Nickel	0,001
% Silicon	0,2 - 0,35	% Vanadium	0,018

#### Typical Mechanical Properties (All weld metal in the as welded condition)

Yield Strength	507 MPa min
Tensile Strength	546 MPa
% Elongation on 50 mm	23 min

#### Typical Current Values (AC 50 OCV min or DC+/-)

Diameter (mm)	Current (A)
2,5	60 - 95
3,15	110 - 130
4,0	140 - 165

#### Packing Data

Diameter (mm)	Electrode Length (mm)	Item Number (1 kg pack)	Item Number (multi-kg pack)	Pack Mass (kg)
2,5	350	W072132	W075132	5,0
3,15	350	W072133	W075133	5,0
4,0	350	W072134	W075134	5,0

## Afrox Afrolux



Afrolux is a heavily coated rutile iron powder electrode for high speed welding of H-V fillets and flat butt joints. Using the touch or free arc techniques, the electrode deposits a very neat, finely rippled weld from which the slag is easily removed. The arc is smooth and stable with very little spatter. Striking and restriking qualities are excellent. Afrolux has a weld metal recovery of approximately 160%.

### Applications

Afrolux is eminently suitable for welding fillet and butt welds in mild steel for general fabrication work.

### Technique

The best results are obtained using the touch welding technique with the electrode held at a sufficient angle to prevent the molten slag from crowding the arc. AC is recommended as it reduces arc blow, particularly at the high currents required with large diameter electrodes.

### Re-drying Procedure

Normally re-drying of Afrolux is not necessary, however the molten slag of damp electrodes will tend to crowd the arc even when the correct technique is used. Damp electrodes should be re-dried at 100-120°C for 1-2 hours.

### Classifications

AWS	A5.1	E7024-1
SABS	455	E5124/-2345
EN ISO	2560	E 42 0 RR 13

### Approvals

Lloyds Register of Shipping Grade D,BF,2m,2Ym,No
American Bureau of Shipping Grade 2
Germanischer Lloyd Grade 2
South African Bureau of Standards

### Typical Chemical Analysis (All weld metal)

% Carbon	0,04 - 0,12	% Sulphur	0,025 max
% Manganese	0,6 - 1,2	% Phosphorous	0,025 max
% Silicon	0,2 - 0,6		

### Typical Mechanical Properties (All weld metal in the as welded condition)

Yield Strength	420 MPa min
Tensile Strength	510 - 560 MPa
% Elongation on 50 mm	22 min
Charpy V-Notch at +20°C	80 J min
Charpy V-Notch at 0°C	60 J min
Charpy V-Notch at -18°C	40 J min

### Typical Current Values (AC 50 OCV min or DC+/-)

Diameter (mm)	Current (A)
2,5	70 - 115
3,15	120 - 155
4,0	160 - 225
5,0	220 - 335
6,3	280 - 390

**Deposition Data**

Note:

- 1) The deposition data given was established at the optimum current rating which would be approximately in the middle of the specified range.
- 2) The mass of weld metal deposited per arc hour is a theoretical value which does not take into account welder efficiency.

Diameter (mm)	Mass of an Electrode (g)	Burn-off Time (sec)	Mass of Metal Deposited per Electrode (g)	Mass of Weld Metal Deposited per Arc Hour (g)	No. Electrodes per kg of Weld Metal	kg Weld Metal per kg of Electrodes
2,5	30,3	63,2	32,7	1 139	48	0,61
3,15	66,9	77,0	54,1	1 944	25	0,61
4,0	102,4	84,9	108,4	2 755	16	0,62
5,0	157,7	91,0	164,3	3 694	8	0,63
6,3	248,0	125,5	250,9	4 735	7	0,66

**Data for Welding Horizontal Fillet Welds**

Diameter (mm)	Throat Thickness (mm)	Current (A)	Arc Time (sec)	Bead Length per Electrode (mm)	Welding Speed (m/h)
2,5	2,9	90	64,8	240	13,3
3,15	3,1	135	88,2	360	14,7
4,0	3,8	200	93,6	432	16,6
5,0	4,1	275	102,0	528	18,6
6,3	5,0	350	132,0	590	16,1

**Packing Data**

Diameter (mm)	Electrode Length (mm)	Approx. No. Electrodes/kg	Pack Mass (kg)	Item Number (multi-kg pack)
2,5	350	30,0	3 x 4,0	W075202
3,15	450	16,0	3 x 5,0	W075203
4,0	450	11,0	3 x 5,0	W075204
5,0	450	7,0	3 x 5,0	W075205
6,3	450	4,0	3 x 5,0	W075207

## Afrox 7018-1



Afrox 7018-1 is an AC/DC all-position basic coated hydrogen-controlled electrode of premium quality. It was designed for applications where fracture toughness and the most severe X-ray requirements in all positions are required. This electrode combines outstanding all-positional welding characteristics, excellent bead profile and appearance in both root and capping passes with a smooth stable arc and quick freezing weld metal. Its ability to operate at lower than normal currents and give a fully penetrating weld bead is of particular significance for root runs which are inaccessible for back gouging. These properties give the electrode outstanding welder appeal.

### Applications

Afrox 7018-1 is used for the welding of a variety of carbon-manganese and low alloy steels used in the fabrication of pressure vessels, pipe work and in general structural fabrication work. It is recommended for applications where severe X-ray requirements and mechanical properties have to be met.

### Technique

As with all basic hydrogen-controlled electrodes, as short an arc as possible should be kept at all times. When starting with a new electrode, the arc should be initiated a short distance

ahead of the start or crater and worked back over this distance before continuing the weld in the required direction. On larger size joints, several stringer beads should be used where possible in preference to one large weaved bead to ensure optimum mechanical properties. DC- should be used for root passes where poor fit-up is a factor to be taken into account.

### Re-drying Procedure

Hydrogen-controlled electrodes must be re-baked prior to use, the baking temperature required being governed by the maximum hydrogen content tolerable in the deposited weld metal. For a maximum of 5-10 ml H<sub>2</sub>/100 g, re-bake at a temperature of 350-370°C for 1-2 hours. (Please consult the section regarding the storage, handling and treatment of low hydrogen electrodes.)

Afrox 7018-1 is manufactured and tested in accordance with the requirements of AWS A5.01. Different class and schedules can be provided upon request.

### Classifications

AWS	A5.1	E7018-1 H8
SABS	455	E5118/-4427H
EN	2560	E 42 4 B 32 H5

### Approvals

Lloyds Register of Shipping Grade DXVu0,BF,3m,3Ym,H15
American Bureau of Shipping Grade 3Y,3H
Germanischer Lloyd Grade 3YH10
TÜV
South African Bureau of Standards

### Typical Chemical Analysis (All weld metal)

% Carbon	0,05 - 0,09	% Sulphur	0,025 max
% Manganese	1,3 - 1,5	% Phosphorous	0,025 max
% Silicon	0,25 - 0,45		

### Typical Mechanical Properties (All weld metal)

As Welded		Stress Relieved (630°C for 8 hours)	
0,2% Proof Stress	420 MPa min	0,2% Proof Stress	350 MPa min
Tensile Strength	510 - 570 MPa	Tensile Strength	485 MPa min
% Elongation on 50 mm	26 min	% Elongation on 50 mm	22 min
Charpy V-Notch at -29°C	130 J min	Charpy V-Notch at -29°C	80 J min
Charpy V-Notch at -46°C	80 J min		

### Typical Current Values (DC+/- for root welds or AC 70 OCV min)

Diameter (mm)	Downhand	Vertical-up	Overhead
2,5	70 - 100	75 - 85	80 - 90
3,15	90 - 135	95 - 110	100 - 110
4,0	135 - 200	140 - 155	145 - 155
5,0	180 - 260	-	-
6,3	245 - 380	-	-

### Deposition Data

Note:

- 1) The deposition data given was established at the optimum current rating which would be approximately in the middle of the specified range.
- 2) The mass of weld metal deposited per arc hour is a theoretical value which does not take into account welder efficiency.

Diameter (mm)	Mass of an Electrode (g)	Burn-off Time (sec)	Mass of Metal Deposited per Electrode (g)	Mass of Weld Metal Deposited per Arc Hour (g)	No. Electrodes per kg of Weld Metal	kg Weld Metal per kg of Electrodes
2,5	21,6	64,2	13,6	761	74	0,62
3,15	33,4	70,0	21,3	1 094	47	0,63
4,0	52,0	71,9	34,0	1 700	30	0,65
5,0	100,3	100,3	67,7	2 428	15	0,67
6,3	150,6	110,5	104,2	3 394	10	0,69

### Data for Welding Horizontal Fillet Welds

Diameter (mm)	Throat Thickness (mm)	Current (A)	Arc Time (sec)	Bead Length per Electrode (mm)	Welding Speed (m/h)
2,5	3,0	85	62,0	165	9,6
3,15	4,2	125	73,0	215	10,6
4,0	5,0	175	80,0	225	10,1
5,0	6,0	225	106,2	287	9,7
6,3	6,9	320	103,2	349	12,2

### Packing Data

Diameter (mm)	Electrode Length (mm)	Approx. No. Electrodes/kg	Pack mass (kg)	Item Number (multi-kg pack)
2,5	350	46	3 x 4,0	W075282
3,15	350	30	3 x 4,0	W075283
4,0	350	19	3 x 4,0	W075284
5,0	450	10	3 x 6,0	W075285
6,3	450	7	3 x 6,0	W075287

### 7018-1 DriPac (2 kg)

Diameter (mm)	Electrode Length (mm)	Downhand	Vertical-up	Overhead	Item Number
2,5	350	70 - 100	75 - 85	80 - 90	W075482
3,15	350	90 - 135	95 - 110	100 - 110	W075483
4,0	350	135 - 200	140 - 155	145 - 155	W075484
5,0	450	180 - 260	-	-	W075485
6,3	450	245 - 380	-	-	W075487

## Afrox 78MR



Specially formulated with a unique moisture resistant coating, 78MR is designed to reduce hydrogen at its primary source – moisture in the electrode coating. This means 78MR starts with a low initial moisture content and moisture regain, after extended exposure to the atmosphere, and is extremely low when compared with conventional hydrogen-controlled electrodes. Aprox 78MR is an AC/DC all-position basic coated hydrogen-controlled electrode which features excellent mechanical properties and low moisture regain rates after baking. The low moisture content of the coating and the high resistance to moisture re-absorption is a major benefit long recognised by manufacturers of critical components where avoidance of hydrogen induced cracking is of crucial importance. Aprox 78MR exhibits outstanding all positional welding characteristics with excellent bead profile and appearance. The arc is smooth and stable, giving a fully penetrating weld bead. The slag release in all positions is excellent and the electrode operates with minimal spatter on both AC and DC. Aprox 78MR is recommended for all structural applications where stringent mechanical properties and X-ray quality joints in all positions are required.

### Applications

Aprox 78MR is recommended for welding a wide range of carbon-manganese and low alloy steels used in structural applications and for the construction of pressure vessels.

Classifications		
AWS	A5.1	E7018-1 H4 R
SABS	455	E5118/-4427H
SANS	2560	E 424 B 12 H10
EN ISO	2560	AE 424 B 12 H10

Approvals
Lloyds Register of Shipping Grade DXVu0,BF,3m,3Ym,H15
American Bureau of Shipping Grade 3Y,3H
Germanischer Lloyd Grade 3YH10
South African Bureau of Standards

Typical Chemical Analysis (All weld metal)			
% Carbon	0,05 - 0,09	% Sulphur	0,025 max
% Manganese	1,25 - 1,5	% Phosphorous	0,025 max
% Silicon	0,25 - 0,45		

Typical Mechanical Properties (All weld metal)	
Yield Strength	420 MPa min
Tensile Strength	510 - 650 MPa
% Elongation on 50 mm	26 min
Charpy V-Notch at -20°C	120 J min
Charpy V-Notch at -29°C	100 J min
Charpy V-Notch at -40°C	80 J min

### Technique

As with all hydrogen-controlled electrodes, as short an arc as possible should be kept at all times. When starting with a new electrode, the arc should be initiated a short distance ahead of the start of the weld or crater and worked back over this distance before continuing the weld in the required direction. On heavier sections, several stringer beads should be used in preference to one large weave bead to ensure optimum mechanical properties.

### Re-drying Procedure

Hydrogen-controlled electrodes must be re-baked prior to use, the baking temperature required being governed by the maximum hydrogen content tolerable in the deposited weld metal. For 5-10 ml H<sub>2</sub>/100 g, re-bake at a temperature of 250-270°C for 1-2 hours, and for <5 ml H<sub>2</sub>/100 g, a temperature of 370-400°C for 1-2 hours. (Please consult the section regarding the storage, handling and treatment of low hydrogen electrodes).

Aprox 78MR is manufactured and tested in accordance with the requirements of AWS A5.1.



**Typical Current Values**  
 (DC+/- or AC 70 OCV min)

Diameter (mm)	Current (A)
2,5	70 - 100
3,15	100 - 150
4,0	140 - 200
5,0	160 - 285
6,3	250 - 390

**Deposition Data**

Note:

- 1) The deposition data given was established at the optimum current rating which would be approximately in the middle of the specified range.
- 2) The mass of weld metal deposited per arc hour is a theoretical value which does not take into account welder efficiency.

Diameter (mm)	Mass of an Electrode (g)	Burn-off Time (sec)	Mass of Metal Deposited per Electrode (g)	Mass of Weld Metal Deposited per Arc Hour (g)	No. Electrodes per kg of Weld Metal	kg Weld Metal per kg of Electrodes
2,5	22,2	66,5	13,7	742	73	0,61
3,15	34,3	71,3	21,5	1 084	47	0,62
4,0	54,6	78,5	34,5	1 582	29	0,63
5,0	108,5	114,3	72,0	2 270	14	0,66
6,3	155,5	116,0	106,9	3 312	10	0,68

**Packing Data**

Diameter (mm)	Electrode Length (mm)	Item Number (1 kg pack)	Approx. No. Electrodes/kg	Pack mass (kg)	Item Number (multi-kg pack)
2,5	350	W072272	45	3 x 4,0	W075272
3,15	350	W072273	29	3 x 4,0	W075273
4,0	350	-	18	3 x 4,0	W075274
5,0	450	-	9	3 x 6,0	W075275
6,3	450	-	6	3 x 6,0	W075277

## Afrox Ferron 1



A basic coated AC/DC hydrogen-controlled electrode for use in all positions. Aprox Ferron 1 has a smooth, stable arc with good striking qualities, a slag which is easily removed and an excellent weld bead profile and appearance. The weld metal deposited is of high metallurgical and radiographic quality and complies with the requirements of the radiographic standard of AWS A5.1 grade 1.

### Applications

Ferron 1 deposits weld metal capable of resisting cracking under conditions of high restraint and is suitable for welding CMn steels and low alloy steels in structural fabrications. The electrode is suitable for welding sulphur bearing steels and components to be vitreously enamelled.

### Technique

As with all basic hydrogen-controlled electrodes, as short an arc as possible should be kept at all times. When starting with a new electrode, the arc should be initiated a short distance

ahead of the start or crater and worked back over this distance before continuing the weld in the required direction. On larger size joints, several stringer beads should be used where possible in preference to one large weaved bead to ensure optimum mechanical properties.

### Re-drying Procedure

Hydrogen-controlled electrodes must be re-baked prior to use, the baking temperature required being governed by the maximum hydrogen content tolerable in the deposited weld metal. For a maximum of 5-10 ml H<sub>2</sub>/100 g, re-bake at a temperature of 350-370°C for 1-2 hours. (Please consult the section regarding the storage, handling and treatment of low hydrogen electrodes).

Ferron 1 is manufactured and tested in accordance with the requirements of AWS A5.1.

### Classifications

AWS	A5.1	E7018 H8
SABS	455	E5118/-3427H
EN	2560	E 42 3 B 32 H5

### Approvals

Lloyds Register of Shipping Grade DXVuD0,BF,3m,3Ym,H15

American Bureau of Shipping Grade 3Y, 3H

South African Bureau of Standards

### Typical Chemical Analysis (All weld metal)

% Carbon	0,05 - 0,09	% Sulphur	0,025 max
% Manganese	1,0 - 1,45	% Phosphorous	0,025 max
% Silicon	0,3 - 0,75		

### Typical Mechanical Properties (All weld metal in the as welded condition)

Yield Strength	420 MPa min
Tensile Strength	510 - 610 MPa
% Elongation on 50 mm	26 min
Charpy V-Notch at -20°C	100 J min
Charpy V-Notch at -29°C	90 J min

### Typical Current Values (DC+/- or AC 70 OCV min)

Diameter (mm)	Current (A)
2,5	70 - 100
3,15	100 - 140
4,0	145 - 180
5,0	190 - 280
6,3	260 - 370

### Deposition Data

Note:

- 1) The deposition data given was established at the optimum current rating which would be approximately in the middle of the specified range.
- 2) The mass of weld metal deposited per arc hour is a theoretical value which does not take into account welder efficiency.

Diameter (mm)	Mass of an Electrode (g)	Burn-off Time (sec)	Mass of Metal Deposited per Electrode (g)	Mass of Weld Metal Deposited per Arc Hour (g)	No. Electrodes per kg of Weld Metal	kg Weld Metal per kg of Electrodes
2,5	22,4	70,3	14,0	716	72	0,62
3,15	35,6	79,9	22,3	1 002	45	0,62
4,0	50,6	71,1	33,3	1 686	31	0,65
5,0	99,8	101,5	69,0	2 447	15	0,69
6,3	157,6	116,9	108,8	3 351	10	0,69

### Data for Welding Horizontal Fillet Welds

Diameter (mm)	Throat Thickness (mm)	Current (A)	Arc Time (sec)	Bead Length per Electrode (mm)	Welding Speed (m/h)
2,5	2,5	85	64,2	146	8,2
3,15	3,1	125	75,0	186	8,9
4,0	5,0	175	69,6	204	10,6
5,0	5,9	225	96,6	258	9,6
6,3	6,0	320	99,0	368	13,4

### Packing Data

Diameter (mm)	Electrode Length (mm)	Approx. No. Electrodes/kg	Pack mass (kg)	Item Number (multi-kg pack)
2,5	350	45	3 x 4,0	W075312
3,15	350	28	3 x 4,0	W075313
4,0	350	20	3 x 4,0	W075314
5,0	450	10	3 x 6,0	W075315
6,3	450	6	3 x 6,0	W075317

## Oerlikon Ferromatic



Heavy coated rutile high-efficiency electrodes with 160% metal recovery. Suitable for container and storage vessel construction, filler and capping runs of multi-layer weldments. Good notch toughness, automatic striking and re-striking, bead can be drawn out. Excellent deslagging characteristics.

### Re-drying Procedure

Provided that electrodes are stored in dry conditions, re-drying is not necessary.

### Classifications

#### Standards

AWS/ASME SF	A 5.1	E7024
EN	2560	E 38 O RR 73

#### Electrode Marking

OER	7024
-----	------

### Approvals

Lloyds Register of Shipping Grade D,BF,1m,NR

### Typical Chemical Analysis (All weld metal)

% Carbon	0,06	% Sulphur	0,03 max
% Manganese	0,7	% Phosphorous	0,03 max
% Silicon	0,35		

### Packing Data

Diameter (mm)	Current (A)	Electrode Length (mm)	Pack Mass (kg)	Pieces per Carton (approx.)	Item Number
2,5	90 - 120	350	5,0	155	W111042
3,15	130 - 160	450	5,0	73	W111043
4,0	180 - 220	450	5,0	46	W111044
5,0	270 - 320	450	5,0	30	W111045
6,3	300 - 360	450	5,0	20	W111046

## Oerlikon Tenacito



Tenacito 7018-1 is a low hydrogen, basic covered electrode for welding medium tensile strength structural and fine grained steels. It has excellent positional weldability and stable arc characteristics.

### Re-drying Procedure

Use dry electrodes only. Re-drying should be carried out at 300-350°C for 2 hours.

### Classifications

#### Standards

AWS	A 5.1	7018-1
EN	2560	E 42 6B 42 H5

#### Electrode Marking

Tenacito	7018-1
----------	--------

### Approvals

Lloyds Register of Shipping Grade DXVu0,BF,3m,3Ym,H15

### Typical Chemical Analysis (All weld metal)

% Carbon	0,07	% Sulphur	<0,02
% Manganese	1,2	% Phosphorous	<0,02
% Silicon	0,4		

### Typical Mechanical Properties (All weld metal in the as welded condition)

Yield Strength	>440 MPa
Tensile Strength	520 - 620 MPa
% Elongation on 5d	>25
Impact Strength at +20°C	>160 J
Impact Strength at 0°C	>150 J
Impact Strength at -20°C	>130 J
Impact Strength at -40°C	>100 J
Impact Strength at -60°C	>50 J

### Packing Data

Diameter (mm)	Current (A)	Electrode Length (mm)	Pack Mass (kg)	Item Number (Tenacito C5)	Item Number (Tenacito)
2,5	65 - 95	350	5,0	W111472	W075372
3,15	90 - 140	350	5,0	W111473	W075373
4,0	140 - 185	450	5,0	W111474	W075374
5,0	185 - 240	450	5,0	W111475	W075375
6,3	240 - 340	450	5,0	-	W111066

## Oerlikon Fincord M



Medium coated, rutile type electrode especially suitable for light gauge sheet welding. When fillet welding, the Fincord M electrode can be kept in contact with the workpiece with no resultant excess convexity. Very little spatter loss. Smooth bead appearance.

### Re-drying Procedure

Provided that electrodes are stored in dry conditions, re-drying is not necessary.

Classifications					
Standards					
AWS/ASME SF	A 5.1	E6013			
EN	2560	E35 A R 11			
Electrode Marking					
OER	6013				
Typical Chemical Analysis (All weld metal)					
% Carbon	0,05	% Sulphur	0,02 max		
% Manganese	0,5	% Phosphorous	0,02 max		
% Silicon	0,45				
Typical Mechanical Properties (All weld metal in the as welded condition)					
0,2% Proof Stress	>360 MPa				
Tensile Strength	450 - 560 MPa				
% Elongation on 5d	>22				
Impact Strength at +20°C	>60 J				
Impact Strength at 0°C	>40 J				
Packing Data					
Diameter (mm)	Current (A)	Electrode Length (mm)	Pack Mass (kg)	Pieces per Carton (approx.)	Item Number
2,5	60 - 90	350	5,0	250	W111002
3,15	90 - 140	350	5,0	170	W111003
4,0	120 - 190	350	5,0	106	W111004
5,0	160 - 240	450	5,0	69	W111005
6,3	200 - 290	450	5,0	32	W111006

## Oerlikon Fincord Plain



Heavy-coated rutile type electrode with outstanding welding characteristics. Suitable for the welding of light gauge steel sheets. Automatic re-striking, self-detaching slag, smooth bead appearance.

### Re-drying Procedure

Provided that electrodes are stored in dry conditions, re-drying is not necessary.

#### Classifications

##### Standards

AWS/ASME SF	A 5.1	E6013
EN	2560	E35 A R 11

##### Electrode Marking

OER	P 6013
-----	--------

#### Typical Chemical Analysis (All weld metal)

% Carbon	0,08	% Sulphur	0,03 max
% Manganese	0,5	% Phosphorous	0,03 max
% Silicon	0,45		

#### Typical Mechanical Properties (All weld metal in the as welded condition)

0,2% Proof Stress	>380 MPa
Tensile Strength	510 - 610 MPa
% Elongation on 5d	>22
Impact Strength at +20°C	>60 J
Impact Strength at 0°C	>50 J
Impact Strength at -20°C	>25 J

#### Packing Data (42 V OCV min)

Diameter (mm)	Current (A)	Electrode Length (mm)	Pack Mass (kg)	Pieces per Carton (approx.)	Item Number
2,0	50 - 70	300	5,0	446	W111012
3,15	100 - 140	350	5,0	140	W111013
4,0	140 - 180	450	5,0	72	W111014
5,0	190 - 240	450	5,0	46	W111015

## Oerlikon Supercord



Rutile-cellulosic type electrode for general assembly work, also for lighter gauge sheet. Highly suitable for sheet metal containers, storage vessels and oil tanks. Excellent all-position weldability including vertical-up and down. Ideal for fillet welding in the vertical-down position. It has a deposition efficiency of 60%.

### Re-drying Procedure

Provided that electrodes are stored in dry conditions, re-drying is not necessary.

#### Classifications

##### Standards

AWS/ASME SF	A 5.1	E6013
EN	2560	E35 A R 11
SABS	455	E4313 / 0415

##### Electrode Marking

Supercord

#### Typical Chemical Analysis (All weld metal)

% Carbon	0,08	% Sulphur	0,03 max
% Manganese	0,5	% Phosphorous	0,03 max
% Silicon	0,3		

#### Typical Mechanical Properties (All weld metal in the as welded condition)

0,2% Proof Stress	>360 MPa
Tensile Strength	450 - 550 MPa
% Elongation on 5d	>22
Impact Strength at +20°C	>60 J
Impact Strength at 0°C	>50 J
Impact Strength at -20°C	>25 J

#### Packing Data (42 V OCV min)

Diameter (mm)	Current (A)	Electrode Length (mm)	Pack Mass (kg)	Pieces per Carton (approx.)	Item Number
2,5	60 - 90	350	5,0	277	W111022
3,15	90 - 140	350	5,0	179	W111023
4,0	140 - 180	350	5,0	110	W111024
5,0	180 - 240	350	5,0	71	W111025



## Oerlikon Overcord



Rutile-cellulosic type electrode for the welding of a large variety of components. It is particularly suitable for the welding of root runs in pipe, for tight joint preparations and for the welding of storage vessels and oil tanks. Overcord has excellent all-position weldability including vertical-up and down and is ideal for fillet welding in the vertical-down position. It has a deposition efficiency of 60%.

### Re-drying Procedure

Provided that electrodes are stored in dry conditions, re-drying is not necessary.

#### Classifications

##### Standards

AWS/ASME SF	A 5.1	E6012
EN	2560	E35 A RC 11

##### Electrode Marking

Overcord

#### Typical Chemical Analysis (All weld metal)

% Carbon	0,08	% Sulphur	0,03 max
% Manganese	0,5	% Phosphorous	0,03 max
% Silicon	0,3		

#### Typical Mechanical Properties (All weld metal in the as welded condition)

0,2% Proof Stress	>360 MPa
Tensile Strength	450 - 560 MPa
% Elongation on 5d	>22
Impact Strength at +20°C	>60 J
Impact Strength at 0°C	>50 J
Impact Strength at -20°C	>25 J

#### Packing Data (42 V OCV min)

Diameter (mm)	Current (A)	Electrode Length (mm)	Pack Mass (kg)	Pieces per Carton (approx.)	Item Number
2,5	60 - 90	350	5,0	277	W111312
3,15	90 - 140	350	5,0	179	W111313
4,0	140 - 180	350	5,0	110	W111314
5,0	180 - 240	350	5,0	71	W111315

## AWS A5.1 Specification for Carbon Steel Electrodes for Shielded Metal Arc Welding

The welding electrodes covered by this specification are classified in terms of the following:

- Type of current
- Type of covering
- Welding position
- Mechanical properties of the weld metal in the as welded condition.

The method of classifying the electrodes is based on the use of a four-digit code preceded by a letter.

The digits signify the following:

### First letter

'E' designates an arc welding electrode.

### Digits 1 and 2

The minimum tensile strength of the weld metal in the as welded condition (x1 000), e.g. as follows:

E60XX

60 000 psi minimum (460 MPa min)

E70XX

70 000 psi minimum (500 MPa min)\*

\*Disparity exists between these two values. Please refer to specification.

### Digits 3 and 4

This indicates the position of welding, the type of flux covering and the kind of welding current. For complete identification of the electrode, it is necessary to read these two digits together as detailed in the table below:

Classification	Position	Current	Coating Type
EXX10	All positions	DC+	Cellulose sodium
EXX11	All positions	AC or DC+	Cellulose potassium
EXX12	All positions	AC or DC-	Rutile sodium
EXX13	All positions	AC or DC+/-	Rutile potassium
EXX14	All positions	AC or DC+/-	Rutile iron powder
EXX15	All positions	DC+	Low hydrogen sodium
EXX16	All positions	AC or DC+	Low hydrogen potassium
EXX18	All positions	AC or DC+	Low hydrogen potassium iron powder
EXX18M	All positions	DC+	Low hydrogen iron powder
EXX19	All positions	AC or DC+/-	Rutile iron oxide
EXX20	Flat and horizontal	AC or DC-	High iron oxide
EXX22	Flat and horizontal	AC or DC-	High iron oxide
EXX24	Flat and horizontal	AC or DC+/-	Rutile iron powder
EXX27	Flat and horizontal	AC or DC-	High iron oxide iron powder
EXX28	Flat and horizontal	AC or DC+	Low hydrogen iron powder

Certain of the low hydrogen electrodes may also have optional designators as detailed below:

- A letter 'M' is used to specify electrodes with greater toughness, low moisture content both in the as received and exposed condition and specific diffusible hydrogen contents
- A letter 'R' is used to identify electrodes that meet the requirements of the specified absorbed moisture test
- An optional supplemental designator 'HZ' indicates an average diffusible hydrogen content of not more than 4, 8, or 16 ml H<sub>2</sub>/100 g of deposited metal when tested
- Electrodes with the following optional supplemental designation shall meet the lower temperature Charpy V-Notch impact requirements specified.

AWS Classification	Electrode Designation	Average Minimum Charpy Impact Values
E7018	E7018-1	27 J at -46°C
E7024	E7024-1	27 J at -18°C

# MIG/MAG Wires

## Afrox MIG 9000 GoldFlo



Afrox MIG 9000 GoldFlo is a premium quality bronze coated MIG wire produced from high quality double deoxidised rod. The higher manganese and silicon levels ensure improved weld metal deoxidation, making Aprox MIG 9000 GoldFlo an excellent choice for welding on metal with a medium to high presence of mill scale or rust. The higher silicon levels promote a smooth bead surface and a flat fillet bead profile with equal leg length and uniform wetting is easily achieved.

The wire is designed for both single- and multi-pass welding in all positions. The bronze coating enhances the shelf life and also ensures good electrical conductivity with reduced friction during high speed welding.

Afrox MIG 9000 GoldFlo has excellent, smooth wire feedability

and is suitable for welding with dip (short circuit), spray arc and pulsed arc transfer using Ar/CO<sub>2</sub> or CO<sub>2</sub> shielding gases.

### Application

Afrox MIG 9000 GoldFlo is recommended for welding of mild and medium tensile strength steels and is an excellent choice for general steel construction, sheet metal applications, pressure vessel fabrication, structural welding and pipe welding.

### Recommended Shielding Gas

Argoshield® Universal. Flow rates of 18-22 l/min should be used.

### Classifications

AWS/ASME-SFA	A5.18	ER 70S-6
EN ISO	14341 (2011)-A-	G 42 4 M21 3Si1

### Approvals

TÜV, DB, BV, ABS, LR

### Chemical Composition (Typical)

% Carbon	0,07	% Sulphur	0,004	% Chromium	0,038
% Manganese	1,45	% Phosphorous	0,013	% Molybdenum	0,06
% Silicon	0,85	% Nickel	0,023	% Copper	0,031

### Typical Mechanical Properties (All weld metal in the as welded condition)

MIG 9000 GoldFlo	Using Argoshield®	Using CO <sub>2</sub>
Yield Strength	452 MPa	420 MPa
Tensile Strength	560 MPa	525 MPa
% Elongation	27	31
Impact Energy, CVN	84 J min av @-30°C	72 J min av @-30°C

### Welding Parameters

Diameter (mm)	Current	
	Amps (A)	Volts (V)
1,0	90 - 253	16 - 31
1,2	120 - 355	18 - 32,5

### Packing Data Aprox MIG 9000 GoldFlo

Diameter (mm)	Weight (kg)	Winding	Item Number
1,0 (spool - S300)	18	Precision PLW	W033972
1,2 (spool - S300)	18	Precision PLW	W033973
1,0 (drum)	250	-	W033992
1,2 (drum)	250	-	W033993

## Afrox MIG 6000/6000 Cert Afrox TIG 70S-6



Afrox MIG 6000 and Afrox TIG 70S-6 are produced from high quality deoxidised rod. The products are copper coated for increased shelf life, which in the case of MIG/MAG wires, also facilitates good electrical conductivity and pick-up with reduced friction during high speed welding. MIG 6000 is a premium quality wire which is precision layer wound to provide positive uninterrupted feeding in semi-automatic and automated systems.

### Welding Procedure

MIG 6000 is suitable for dip (short arc), spray arc and pulsed arc transfer welding using shielding gases such as Argoshield®

5, Argoshield® Light, Argoshield® Heavy and Argoshield® Universal as well as CO<sub>2</sub>. Gas flow rates of 15 ℓ/min at low currents rising to 20 ℓ/min at high currents should be used. TIG 70S-6 rods should be used with a 2% thoriated non-consumable electrode with pure argon as a shielding gas at flow rates of 10-15 ℓ/min.

### Identification

TIG 70S-6 – Red colour tip and hard stamped 70S-6.

MIG 6000 Cert in 1,0 and 1,2 mm & TIG 70S-6 are manufactured and tested in accordance with the requirements of AWS A5.01.

### Classifications

AWS	A5.18	ER 70S-6
SABS	145	Grade A
EN ISO	14341	G42 2 C G4Si1
EN ISO	636-A	W 42 3 W4Si1
EN ISO	636-B	W 49 A 4 W4Si1

### Approvals

#### MIG 6000

Lloyds Register of Shipping Grade DXVud,BF,2S,2YS,H15

American Bureau of Shipping Grade 2SA

South African Bureau of Standards

TÜV

### Typical Chemical Analysis (All weld metal)

% Carbon	0,07 - 0,15	% Sulphur	0,035 max
% Manganese	1,4 - 1,85	% Phosphorous	0,03 max
% Silicon	0,8 - 1,15	% Copper	0,4 max (typical 0,18)

### Typical Mechanical Properties (All weld metal in the as welded condition)

MIG 6000 with CO <sub>2</sub> as Shielding Gas	As Welded	Stress Relieved 650°C/15 hr	Normalised 920°C/0,5 hr
0,2% Proof Stress	430 MPa min	360 MPa min	315 MPa min
Tensile Strength	510 - 570 MPa	490 - 570 MPa	470 - 550 MPa
% Elongation on 50 mm	26 min	26 min	26 min
Charpy V-Notch at +20°C	110 J min	110 J min	80 J min
Charpy V-Notch at 0°C	80 J min	-	-
Charpy V-Notch at -20°C	47 J min	47 J min	47 J min

**Typical Mechanical Properties (All weld metal in the as welded condition)**

TIG 70S-6 with Argon as Shielding Gas	As Welded
0,2% Proof Stress	420 MPa min
Tensile Strength	510 - 570 MPa
% Elongation on 50 mm	26 min
Charpy V-Notch at +20°C	110 J min
Charpy V-Notch at -29°C	50 J min
Charpy V-Notch at -46°C	27 J min

**Packing Data  
MIG 6000**

Diameter (mm)	Approx. Length of Wire/kg (m)	Item Number
0,8	245	W033900
0,9	186	W033901
1,0	160	W033902
1,2	110	W033903
1,6	63	W033905

**MIG 6000 Cert**

1,0	160	W033912
1,2	110	W033913

The wire is layer wound onto wire basket spools having a nominal mass of 18 kg

**Packing Data  
TIG 70S-6**

Diameter (mm)	Consumable Length (mm)	Item Number
1,6	950	W030501
2,0	950	W030502
2,4	950	W030503

TIG rods are supplied in 5 kg tubes

## Afrox Megapac



Afrox Megapac is a bulk MIG/MAG wire system designed specifically to enhance the performance of automated welding systems. The wire is introduced into the drum by using a unique reverse twist coiling method, which ensures that the wire emerges from the container virtually straight. This facilitates the precise positioning of the robot, which in turn enhances weldability and accuracy, while reducing wear on liners and contact tips. In addition, the negative effects of the cast and/or helix which can be experienced with conventionally spooled reels is eliminated. Each Megapac contains approximately 230 kg of wire, which is equivalent to approximately 13 standard spools. With an estimated

changeover time of 15 minutes a spool, this amounts to an added three hours production time for every Megapac used. Aprox Megapac not only offers reduced equipment downtime, but also vastly improves production efficiency. Megapac containers, which are 820 mm high with a diameter of 510 mm, occupy only a small area on the shop floor. The hood, through which the wire is fed from the drum, not only keeps the wire free from dust and dirt but also obviates the need for pay-off devices which are essential when other bulk packages are used. Megapac contains copper coated wire identical to MIG 6000.

### Classifications

AWS	A5.18	ER 70S-6
SABS	145	Grade A
EN	14341	G42 2 C G4Si1

### Approvals

Lloyds Register of Shipping DxVud,BF,2S,2YS,H15

American Bureau of Shipping 2SA

South African Bureau of Standards

TÜV

### Typical Chemical Analysis (All weld metal)

% Carbon	0,07 - 0,15	% Sulphur	0,035 max
% Manganese	1,4 - 1,85	% Phosphorous	0,03 max
% Silicon	0,8 - 1,15	% Copper	0,4 max (typical 0,18%)

### Typical Mechanical Properties (All weld metal using CO<sub>2</sub> gas)

0,2% Proof Stress	430 MPa min
Tensile Strength	510 - 570 MPa
% Elongation on 50 mm	26 min
Charpy V Notch at +20°C	110 J min
Charpy V-Notch at 0°C	80 J min
Charpy V-Notch at -20°C	47 J min

### Packing Data

Diameter (mm)	Item Number
0,9	W033951
1,0	W033952
1,2	W033953

### Packing Data

Description	Item Number
Megapac Liner (per metre)	W033982
Megapac Liner Connection Kit	W033983
Megapac Hood 510	W033985

## Afrox MIG 3000 PLUS



Afrox MIG 3000 PLUS is a mild steel welding wire produced from high quality double deoxidised rod. The wire is copper coated for increased shelf life.

### Welding Procedure

MIG 3000 PLUS exhibits a low spatter volume and is suitable for dip, spray arc and pulsed arc transfer welding using shielding gases such as Argoshield® 5, Argoshield® Light, Argoshield® Heavy and Argoshield® Universal or CO<sub>2</sub>. Shielding gas flow rates of 15-20 l/min should be used.

### Classifications

AWS	A5.18	ER 70S-6
SABS	145	Grade A
BS EN	14341	G42 2 C G4Si1

### Typical Chemical Analysis (All weld metal)

% Carbon	0,07 - 0,15	% Sulphur	0,035 max
% Manganese	1,4 - 1,85	% Phosphorous	0,03 max
% Silicon	0,8 - 1,15		

### Typical Mechanical Properties (All weld metal using CO<sub>2</sub> gas)

Shielding Gas	CO <sub>2</sub>
Testing Condition	As welded
0,2% Proof Stress	430 MPa min
Tensile Strength	510 - 570 MPa
% Elongation on 50 mm	26 min
Charpy V-Notch at +20°C	110 J min
Charpy V-Notch at 0°C	80 J min
Charpy V-Notch at -20°C	47 J min

### Packing Data

Diameter (mm)	Item Number
0,9 (plastic spool)	W033931
1,0 (plastic spool)	W033942
1,2 (plastic spool)	W033943

## Afrox 250 kg ER70S-6 Drum



Afrox 250 kg ER70S-6 is a mild steel welding wire produced from high quality double deoxidised rod. The wire is copper coated for increased shelf life. Available in a 250 kg drum for increased production.

Argoshield® Heavy and Argoshield® Universal, or CO<sub>2</sub>. Shielding gas flow rates of 15-20 l/min should be used.

### Welding Procedure

Afrox 250 kg ER70S-6 exhibits a low spatter volume and is suitable for dip, spray arc and pulsed arc transfer welding using shielding gases such as Argoshield® 5, Argoshield® Light,

#### Classifications

AWS	A5.18	ER 70S-6
SABS	145	Grade A
BS EN	14341	G42 2 C G4Si1

#### Typical Chemical Analysis (All weld metal)

% Carbon	0,07 - 0,15	% Sulphur	0,035 max
% Manganese	1,4 - 1,85	% Phosphorous	0,03 max
% Silicon	0,8 - 1,15		

#### Typical Mechanical Properties (All weld metal using CO<sub>2</sub> gas)

Shielding Gas	CO <sub>2</sub>
Testing Condition	As welded
0,2% Proof Stress	430 MPa min
Tensile Strength	510 - 570 MPa
% Elongation on 50 mm	26 min
Charpy V-Notch at +20°C	110 J min
Charpy V-Notch at 0°C	80 J min
Charpy V-Notch at -20°C	47 J min

#### Packing Data

Diameter (mm)	Item Number
1,0 (250 kg drum)	W033962
1,2 (250 kg drum)	W033963



# MIG & TIG Wires for CMn & Low Alloy Steels

## AWS A5.18 Specification for Carbon Steel Electrodes and Rods for Gas Shielded Arc Welding

The solid electrodes (and rods) covered by this specification are classified according the following attributes:

- Chemical composition of the electrode
- Mechanical properties of the weld metal.

### Classification Designators

ER 70S-YX	
ER	Indicates a solid wire
70 or 48	The minimum tensile strength of the deposited weld metal. In all specified products in this standard, the minimum tensile strength is 70 000 psi or 480 MPa
S	Solid electrode/wire, a 'C' would indicate a metal cored wire
Y	This can be 2, 3, 4, 5, 6, 7 or 'G' as detailed in the table below
X	This final 'X' shown in the classification represents a 'C' or 'M' which corresponds to the shielding gas with which the metal cored wire is classified. The use of 'C' designates 100% CO <sub>2</sub> shielding, 'M' designates 75-80% Ar/CO <sub>2</sub> . Solid wires are classified using CO <sub>2</sub>

Chemical Composition Requirements for Solid Electrodes and Rods								
Electrode Classification		%C	%Mn	%Si	%S	%P	%Cu	Other
US	Metric							
ER70S-2	ER48S-2	0,07	0,9 - 1,4	0,4 - 0,7	0,035	0,025	0,5	Ti 0,05 - 0,15, Zr 0,02 - 0,12, Al 0,05 - 0,15
ER70S-3	ER48S-3	0,06 - 0,15	0,9 - 1,4	0,45 - 0,75	0,035	0,025	0,5	
ER70S-4	ER48S-4	0,07 - 0,15	1,0 - 1,5	0,65 - 0,85	0,035	0,025	0,50	
ER70S-5	ER48S-5	0,07 - 0,19	0,9 - 1,4	0,3 - 0,6	0,035	0,025	0,5	Al 0,5 - 0,9
ER70S-6	ER48S-6	0,06 - 0,15	1,4 - 1,85	0,8 - 1,15	0,035	0,025	0,5	
ER70S-7	ER48S-7	0,07 - 0,15	1,5 - 2,0	0,5 - 0,8	0,035	0,025	0,5	
ER70S-G	ER48S-G	Not specified						

Single values are maximums. Please consult specification for definitive values

Please Note: AWS now makes provision for metric values. The specification containing equivalent metric values is indicated by AWS A5.18M

# Flux & Metal Cored Wires

## Hobart Fabcor 791



Hobart Fabcor 791 is a gas shielded flux cored wire for welding carbon-manganese steels having a tensile strength up to 620 MPa and where impact properties at sub-zero temperatures may be required. It also has low spatter levels and the slag is easy to remove. The wire is recommended for single- and multi-pass welding in all positions using a 75% Ar/25% CO<sub>2</sub> argon-based mixed gas (Afrox Fluxshield®) or CO<sub>2</sub>. TM-791 has

excellent welder appeal with superior mechanical properties. It has a quiet soft arc with very low spatter and fume levels. Deposited weld metal has similar mechanical properties to that of a 7018 type MMA electrode. These features, along with the high deposition rates inherent in out-of-position welding, make TM-791 an excellent choice for shipbuilding, pressure vessel fabrication and structural welding.

Classifications		
AWS	A5.20	E71T-1, E71T-1M
AWS	A5.20	E71T-9, E71T-9M

Approvals
Lloyds Register of Shipping Grade 3YSH 10
American Bureau of Shipping 3SA, 3YSA HH,(75Ar/25CO <sub>2</sub> ),3YSA HH (CO <sub>2</sub> )
Det Norske Veritas 111Y40MS (H10)
Bureau Veritas SA 3YM HH
Germanischer Lloyd 3YH10S

Typical Chemical Analysis (All weld metal)					
Shielding Gas	Fluxshield®	CO <sub>2</sub>	Shielding Gas	Fluxshield®	CO <sub>2</sub>
% Carbon	0,022	0,021	% Sulphur	0,01	0,011
% Manganese	1,6	1,3	% Phosphorous	0,014	0,015
% Silicon	0,82	0,69			

Typical Mechanical Properties (All weld metal using CO <sub>2</sub> gas)		
Shielding Gas	Fluxshield®	CO <sub>2</sub>
Yield Strength	592 MPa	546 MPa
Tensile Strength	662 MPa	605 MPa
% Elongation on 50 mm	26	28
Charpy V-Notch at -18°C	80 J	95 J
Charpy V-Notch at -29°C	68 J	69 J

**Welding Data  
(DC+) Shielding Gas: Fluxshield®**

Diameter (mm)	Position	Current		Deposition Rates (kg/h)	Electrode Stick Out (mm)
		Amps (A)	Volts (V)		
1,2	Flat/horizontal	250	26	4,1	12,0
1,2	Vertical-up/ overhead	170 - 220	22 - 24	2,0 - 3,5	12,0
1,6	Flat	360	27	5,5 - 3,6	25,0
1,6	Horizontal	280	24	3,6	25,0
1,6	Vertical-up/ overhead	215 - 245	22 - 23	2,6 - 3,0	25,0

**Welding Data  
(DC+) Shielding Gas: CO<sub>2</sub>**

Diameter (mm)	Position	Current		Deposition Rates (kg/h)	Electrode Stick Out (mm)
		Amps (A)	Volts (V)		
1,2	Flat/horizontal	260	27	4,1	12,0
1,2	Vertical-up/ overhead	170 - 220	23 - 25	2,0 - 3,4	12,0
1,6	Flat	360	29 - 26	5,5 - 3,6	25,0
1,6	Horizontal	280	26	3,6	25,0
1,6	Vertical-up/ overhead	215 - 245	24 - 25	2,6 - 3,0	25,0

**Packing Data**

Diameter (mm)	Pack Mass Drums (kg)	Item Number
1,2	15,0	W081051
1,6	15,0	W081052

## Afrox Coremax 71 Plus



Coremax 71 Plus is a gas shielded flux cored wire for welding carbon-manganese steels, having a tensile strength of up to 620 MPa and where impact properties of sub-zero may be required. It has low spatter levels and the slag is easy to remove. The wire is recommended for single- and multi-pass welding in all positions using a 75% Ar, 25% CO<sub>2</sub> argon based mixed gas (Afrox Fluxshield®) or CO<sub>2</sub>.

### Classifications

AWS	A5.20	E71T-1M
-----	-------	---------

### Approvals

Det Norske Veritas
Bureau Veritas

### Typical Chemical Analysis (All weld metal)

% Carbon	0,04	% Sulphur	0,01
% Manganese	1,32	% Phosphorous	0,02
% Silicon	0,42		

### Typical Mechanical Properties (All weld metal using CO<sub>2</sub> gas)

Yield Strength	540 MPa
Tensile Strength	580 MPa
% Elongation on 5d	28
Charpy V-Notch at -18°C	65 J

### Welding Data (DC+) Shielding Gas: 75% Ar/25% CO<sub>2</sub> or CO<sub>2</sub>

Diameter (mm)	Position	Current		Deposition Rates (kg/h)	Electrode Stick Out (mm)
		Amps (A)	Volts (V)		
1,2	Flat/horizontal	260	27	4,1	12
1,2	Vertical-up/ overhead	170 - 220	23 - 25	2,0 - 3,4	12
1,6	Flat	360	29	5,5	25
1,6	Horizontal	280	26	3,6	25
1,6	Vertical-up/ overhead	215 - 245	24 - 25	2,6 - 3,0	25

### Packing Data

Diameter (mm)	Spool Mass (kg)	Item Number
1,2	15,0	W081230
1,6	15,0	W081231

## Afrox S71T-11



S71T-11 is an open-arc (no shielding gas required) tubular wire which is exceptionally easy to use. It is recommended for use with smaller MIG machines or in areas where the provision of gas cylinders is not practical. S71T-11 has little tendency to burn through and is well suited for butt, fillet and lap joints on steel thicknesses of 1,6 mm to 10 mm. It is not recommended for welding steel thicknesses greater than 12 mm.

#### Classifications

AWS	A5.20	E71T-11
EN	17632-A	T 42 Z W N 1 H10

#### Typical Chemical Analysis (All weld metal)

% Carbon	0,18	% Sulphur	0,012
% Manganese	1,0	% Phosphorous	0,012
% Silicon	0,25	% Aluminium	0,8

#### Typical Mechanical Properties (All weld metal using CO<sub>2</sub> gas)

Yield Strength	430 MPa
Tensile Strength	520 MPa
% Elongation on 5d	23

#### Welding Data (DC+) Shielding Gas: CO<sub>2</sub>

Diameter (mm)	Current	
	Amps (A)	Volts (V)
0,8	50 - 200	12 - 24
0,9	70 - 220	13 - 27
1,2	90 - 310	16 - 35

Typical Values

#### Packing Data

Diameter (mm)	Spool Mass (kg)	Item Number
0,8	4,5	W081004
0,9	4,5	W081009
1,2	4,5	W081016

## Hobart Fabshield 4



Hobart Fabshield 4 is an outstanding high deposition self-shielded tubular wire that is used to weld mild and medium carbon steels. It is ideal for either single- or multi-pass welding, and provides outstanding performance with deposition rates of up to 20 kg/h and deposition efficiencies of 84% or better. This electrode produces a globular type transfer with an arc

that is not affected by drafts or moderate wind. It is specifically designed to desulphurise the weld metal and resist cracking. The product is recommended for applications such as machine fabrication, certain ship equipment, industrial and heavy equipment repair.

### Classifications

AWS	A5.20	E70T-4
EN	17632-A	T 46 Z W N 4 H10

### Approvals

American Bureau of Shipping E70T-4 (AWS A5.20)

Canadian Welding Bureau E4802T-4-CH

### Typical Chemical Analysis (All weld metal)

% Carbon	0,27	% Phosphorous	0,008
% Manganese	0,45	% Aluminium	1,36
% Silicon	0,3	% Nickel	0,01
% Sulphur	0,004		

### Typical Mechanical Properties (All weld metal using CO<sub>2</sub> gas)

Yield Strength	476 MPa
Tensile Strength	635 MPa
% Elongation on 50 mm	22

### Welding Data (DC+)

Diameter (mm)	Position	Current		Optimum Settings		Deposition Rates (kg/h)	Electrode Stick Out (mm)
		Amps (A)	Volts (V)	Amps (A)	Volts (V)		
2,0	Flat/horizontal	290 - 370	31	330	30	5,0 - 7,3	50,0
2,4	Flat/horizontal	250 - 500	28 - 34	400	31	4,0 - 12,7	65,0

### Packing Data

Diameter (mm)	Pack Mass (kg)	Package	Item Number
2,0	22,0	Coil	W081033
2,4	22,0	Coil	W081011
2,4	270,0	Drum	W081012

## Hobart Fabshield 21B



Hobart Fabshield 21B is a versatile tubular wire with excellent operator appeal because of its smooth arc, low spatter and overall ease of handling. With no shielding gas needed, it is a good choice for welding in hard-to-reach locations or where the provision of gas cylinders is not practical. It is a good wire for applications where windy or other adverse conditions prevail and where mechanical properties are of less concern. Fabshield 21B has little tendency to burn through and is

well suited for butt, fillet and lap joints on steel thicknesses from 1,6-10 mm. It is not recommended for welding steel thicknesses greater than 12,7 mm. When welding on steels in the 10-19 mm thickness range, a preheat temperature of 160°C is advisable. The wire is recommended for single-pass and limited multiple-pass welding in all positions, using no shielding gas.

### Classifications

AWS	A5.20	E71T-11
EN	17632-A	T 42 Z W N 1 H10

### Approvals

American Bureau of Shipping E71T-11 (AWS A5.20)

### Typical Chemical Analysis (All weld metal)

% Carbon	0,3	% Sulphur	0,003
% Manganese	0,49	% Phosphorous	0,009
% Silicon	0,15	% Aluminium	1,18

### Typical Mechanical Properties (All weld metal using CO<sub>2</sub> gas)

Yield Strength	442 MPa
Tensile Strength	628 MPa
% Elongation on 50 mm	21

### Welding Data (DC+)

Diameter (mm)	Position	Current		Optimum Settings		Deposition Rates (kg/h)	Electrode Stick Out (mm)
		Amps (A)	Volts (V)	Amps (A)	Volts (V)		
1,6	Flat/horizontal	125 - 300	19 - 20	230	17	0,5 - 3,3	12,0 - 19,0
1,6	Vertical/overhead	125 - 250	15 - 19	175	16	0,7 - 2,1	12,0 - 19,0
2,0	Flat/horizontal	175 - 350	16 - 22	275	19	1,1 - 3,0	12,0 - 19,0

### Packing Data

Diameter (mm)	Pack Mass (kg)	Package	Item Number
1,6	15,0	Spool	W081013
2,0	15,0	Spool	W081015
2,0	22,0	Coil	W081014

## Hobart/Fabcor 86R



Hobart/Fabcor 86R is a gas shielded metal cored wire designed for semi-automatic, automatic and robotic welding of low and medium carbon steels. The wire is recommended for single and limited multi-pass welding in the flat and horizontal positions. The recommended shielding gas is Afrox Fluxshield® (75% Ar, 25% CO<sub>2</sub>) at a gas flow rate of 17-24 l/min. Metalloy 76 produces high quality welds with virtually no residual slag.

The product features lower spatter and higher strength levels. The higher manganese content gives increased deoxidisation and greater tolerance to mill scale and paint primers on the workpiece. Penetration is superior to that of solid wires, thereby minimising the cold lap problem on heavier sections of steels. Low spatter and low slag volume combine to greatly reduce clean-up costs.

### Classifications

AWS	A5.18	E70C-6M H4
EN	17632-A	T 50 Z M M 2 H5

### Approvals

Lloyds Register of Shipping 3S,3440SH15  
 American Bureau of Shipping 3SA, 3YSM  
 Det Norske Veritas 111 Y40MS  
 Bureau Veritas SA 3YM  
 Germanischer Lloyd 3Y40H5S  
 Canadian Welding Bureau E4801C-6-CH

### Typical Chemical Analysis (All weld metal)

% Carbon	0,06	% Sulphur	0,019
% Manganese	1,64	% Phosphorous	0,012
% Silicon	0,75		

### Typical Mechanical Properties (All weld metal using CO<sub>2</sub> gas)

Yield Strength	559 MPa
Tensile Strength	628 MPa
% Elongation on 50 mm	27
Charpy V-Notch at -18°C	72 J

### Welding Data (DC+)

Diameter (mm)	Position	Current		Optimum Settings		Deposition Rates (kg/h)	Electrode Stick Out (mm)
		Amps (A)	Volts (V)	Amps (A)	Volts (V)		
1,2	Flat/horizontal	200 - 350	27 - 35	300	32	2,7 - 7,0	12,0 - 19,0
1,6	Flat/horizontal	300 - 450	29 - 34	400	32	5,0 - 9,5	25,0 - 30,0

### Packing Data

Diameter (mm)	Spool Mass (kg)	Item Number
1,2	15,0	W081029
1,6	15,0	W081028



## Coremax 70



Coremax 70 is a metallic flux cored wire designed to be used with Ar/CO<sub>2</sub> (Afrox Fluxshield®) for mild steel and 490 N/mm<sup>2</sup> high tensile steel. Its deposition rate is 10-30% higher than a solid wire.

Multi-layer welding can be performed without removing slag. It is suitable for the multi-layer welding of thick plate welding in such applications as: steel structures, bridges, shipbuilding, vehicles and storage tanks, etc.

### Classifications

AWS	A5.18	E70C-6M
EN	499	E 42 3 B 3 2 H10

### Typical Chemical Analysis (All weld metal)

% Carbon	0,04	% Phosphorous	0,02
% Manganese	1,5	% Sulphur	0,01
% Silicon	0,63		

### Typical Mechanical Properties (All weld metal)

Tensile Strength	598 MPa
Yield Strength	559 MPa
% Elongation	26
Impact Energy at -20°C	57 J
Impact Energy at -30°C	45 J

### Welding Data (DC+)

Diameter (mm)	Current		Flow Rate (ℓ/min)	Pack Mass (kg)	Item Number
	Amps (A)	Volts (V)			
1,2	200 - 300	28 - 38	15 - 25	15,0	W082230
1,6	250 - 400	28 - 38	20 - 25	15,0	W082231

## Fluxofil M10



Fluxofil M10 is a seamless copper coated metal cored wire with outstanding welding properties in the short arc and spray arc ranges depositing slag free weld metal. Almost spatter-free when welding in the spray arc range. Good restriking, even with a cold wire tip, thus being suitable for robotic applications. Characteristic features: good side wall fusion, smooth and finely rippled welds without undercut into the base metal. Little formation of silicates on top of weld, so that

multi-pass welds can be made without inter-run cleaning. Due to an easily controllable weld pool in the short arc range, Fluxofil M10 is well suited for root and positional welding.

### Storage

Keep dry and avoid condensation.

### Classifications

AWS	A5.18	E70C-6M H4
EN ISO	17632-A	T 46 4 M M 1 H5

### Approvals

American Bureau of Shipping	Germanischer Lloyd
Bureau Veritas	Lloyds Register of Shipping
DB	TÜV
Det Norske Veritas	UDT

### Typical Chemical Analysis (All weld metal)

% Carbon	0,06	% Silicon	0,6
% Manganese	1,3		

### Typical Mechanical Properties (All weld metal)

Heat Treatment	As Welded	PWHT 580°C x 2 hr/furnace
Yield Strength N/mm <sup>2</sup>	≥460	≥460
Tensile Strength N/mm <sup>2</sup>	550 - 660	550 - 660
% Elongation on A5	≥24	≥24
Impact Energy at -20°C	≥47 J	≥47 J

Gas Test	Afrox Fluxshield®
Shielding Gas	Afrox Fluxshield®
Materials	S(P)460-S(P)500, S550, HY 80

### Packing Data

Diameter (mm)	Item Number
1,6	W125412

# Cored Wires for CMn & Low Alloy Steels

## Oerlikon Fluxofil 14 HD



Fluxofil 14 HD is a seamless copper coated rutile flux cored wire with a higher filling degree resulting in a higher current carrying capacity and high deposition rate. The welding speed is increased which leads to a saving of time and reduction of costs. It can be used in all positions with only one welding parameter setting (24 V, wire feed = 9 m/min, wire dia. 1,2 mm). Fluxofil 14 HD is used for manual welding, as well as in fully mechanised. It is recommended that a mixed shielding

gas be used and is characterised by low spatter loss, good slag removal and finely rippled, pore-free welds without undercut.

### Storage

Keep dry and avoid condensation.

### Classifications

AWS	A5.20	E71T-1 H4 / E71T-1M H4
EN	17632-A	T 46 2 P M 1 H5

### Approvals

American Bureau of Shipping	Lloyds Register of Shipping
Bureau Veritas	PRS
DB	RS
Det Norske Veritas	TÜV
Germanischer Lloyd	UDT

### Typical Chemical Analysis (All weld metal)

% Carbon	0,05	% Silicon	0,55
% Manganese	1,2		

### Typical Mechanical Properties (All weld metal)

Heat Treatment	As welded
Yield Strength N/mm <sup>2</sup>	460
Tensile Strength N/mm <sup>2</sup>	550 - 650
% Elongation on A5	22
Impact Energy at -20°C	80 J

Gas Test	Afrox Fluxshield®
Shielding Gas	Afrox Fluxshield®
Materials	S(P)235-S(P)460, GP240-GP280 Shipbuilding steels A,B,D,E,AH32 to EH36

### Packing Data

Diameter (mm)	Item Number
1,2	W125133
1,6	W125134

## Oerlikon Fluxofil 19 HD



Fluxofil 19 HD is a seamless copper coated rutile flux cored wire with an enhanced degree of fill. Due to its easily controllable weld pool, the welding characteristics are outstanding. It can be welded in all positions with only one parameter setting (24 V, wire feed 9 m/min, wire diameter 1,2 mm). The enhanced degree of filling results in increased current carrying capacity and deposition rate, thus increasing

welding speed and leading to a saving of time and costs. Low spatter loss, easy slag removal, smooth and finely rippled welds are produced without undercut into the base metal.

### Storage

Keep dry and avoid condensation.

### Classifications

AWS	A5.20	E71T-1 H4
EN	17632-A	T 46 2 P C 1 H5

### Approvals

American Bureau of Shipping	Lloyds Register of Shipping
Bureau Veritas	PRS
DB	RINA
Det Norske Veritas	RS
Germanischer Lloyd	TÜV

### Typical Chemical Analysis (All weld metal)

% Carbon	0,05	% Silicon	0,5
% Manganese	1,20		

### Typical Mechanical Properties (All weld metal)

Heat Treatment	As welded
Yield Strength N/mm <sup>2</sup>	460
Tensile Strength N/mm <sup>2</sup>	550 - 650
% Elongation on A5	22
Impact Energy at -20°C	80 J

Gas Test	CO <sub>2</sub>
Shielding Gas	CO <sub>2</sub>
Materials	S(P)235-S(P)460, GP240-GP280 Shipbuilding steels A,B,D,E,AH32 to EH36

### Packing Data

Diameter (mm)	Item Number
1,2	W125150
1,6	W125152

## AWS A5.20 Specification for Carbon Steel Electrodes for Flux Cored Arc Welding

In this specification, electrodes are classified on the basis of:

- Whether CO<sub>2</sub> is used as a shielding gas
- Suitability for single or multiple-pass application
- Type of current
- Welding position
- Mechanical properties of the deposited weld metal.

The system for identifying the electrode classification in AWS A5.20 follows, for the most part, the standard pattern used in other AWS filler metal specification.

### Classification Designators

EXX-TWMJ HZ	
E	Designates an electrode
First X	This designator is either 6 or 7. It indicates the minimum tensile strength (in psi x 10 000) of the weld metal when the sample is prepared in the manner prescribed by AWS A5.20
Second X	Indicates the primary welding position for which the electrode is designed: 0 - flat and horizontal positions 1 - all positions
T	This designator indicates that the electrode is a flux cored electrode
W	This designator is a number from 1 through 14 or the letter 'G' with or without an 'S' following. The number refers to the usability of the electrode. The 'G' indicates that the external shielding, polarity and impact properties are not specified. The 'S' indicates that the electrode is suitable for single-pass welding only. Please see table below for details
M	An 'M' designator in this position indicates that the electrode is classified using 75-80% Ar-CO <sub>2</sub> shielding gas. When this designator does not appear, it signifies that the shielding gas used for classification is CO <sub>2</sub> or that the product is a self-shielded type
J	Optional supplementary designator. Designates that the electrode meets the requirements for improved toughness by meeting a Charpy impact value of 27 J at -40°C. Absence of the 'J' indicates normal impact requirements
HZ	Optional supplementary designator. Designates that the electrode meets the requirements of the diffusible hydrogen test, (i.e 4, 8 or 16 ml of H <sub>2</sub> per 100 g of deposited weld metal)

Wire Characteristics (Designator W)		
AWS Classification a	External Shielding Medium	Current and Polarity
EXXT-1 (multiple-pass)	CO <sub>2</sub> b	DC, electrode positive
EXXT-2 (single-pass)	CO <sub>2</sub> b	DC, electrode positive
EXXT-3 (single-pass)	None	DC, electrode positive
EXXT-4 (multiple-pass)	None	DC, electrode positive
EXXT-5 (multiple-pass)	CO <sub>2</sub> b	DC, electrode positive
EXXT-6 (multiple-pass)	None	DC, electrode positive
EXXT-7 (multiple-pass)	None	DC, electrode negative
EXXT-10 (single-pass)	None	DC, electrode negative
EXXT-11 (multiple-pass)	None	DC, electrode negative
EXXT-G (multiple-pass)	c	c
EXXT-GS (single-pass)	c	c

a, b and c refer to specification

# Subarc Wires & Fluxes

## Afrox Sub 70-1



Afrox Sub 70-1 is a copper coated CMn submerged arc welding wire for joining carbon-manganese steels. It is widely used in structural steel work, i.e. shipbuilding, construction work, etc. The wire is suitable for both single-pass and multi-pass welding, and for welding butt and fillet joints where maximum ductility is required.

### Classifications

AWS	A5.20	EL12
EN	756	SI

### Typical Chemical Analysis (Wire)

% Carbon	0,05 - 0,12	% Phosphorous	0,025 max
% Manganese	0,4 - 0,6	% Sulphur	0,025 max
% Silicon	0,07 max	% Copper	0,3 max

### Packing Data

Diameter (mm)	Item Number (25 kg coil)
2,0	W080011
2,4	W080012
3,15	W080013
4,0	W080014

## Afrox Sub 70-2



Afrox Sub 70-2 is a copper coated low carbon, medium manganese wire that produces a higher tensile strength weld than Sub 70-1 depending on flux and procedure used. It is recommended for single- and multiple-pass welding.

#### Classifications

AWS	A5.17	EM12K
EN	756	S2

#### Typical Chemical Analysis (Wire)

% Carbon	0,08 - 0,15	% Phosphorous	0,025 max
% Manganese	0,8 - 1,2	% Sulphur	0,025 max
% Silicon	0,1 - 0,2	% Copper	0,3 max

#### Packing Data

Diameter (mm)	Item Number (25 kg coil)	Item Number (68 kg coils)	Item Number (450 kg pay-off spools)	Item Number (300 kg pay-off drums)
2,5	W080052	-	W080057	W080062
3,15	W080053	W080067	W080058	W080063
4,0	W080054	W080068	W080059	W080064
5,0	W080055	-	W080060	-

## Afrox Subarc S3Si



Subarc S3Si is a copper coated submerged arc welding wire containing 1,5% manganese and 0,3% silicon. It is recommended for use with basic fluxes such as HPF-N90 where exceptional sub-zero impact properties are required.

### Classifications

EN	756	S3Si
AWS	A5.17	EH12K

### Typical Chemical Analysis (All weld metal)

% Carbon	0,08 - 0,15	% Phosphorous	< 0,3
% Manganese	1,4 - 1,8	% Sulphur	< 0,01
% Silicon	0,2 - 0,35	% Copper	< 0,01

### Packing Data

Diameter (mm)	Item Number (27 kg coil)
2,4	W078116
3,2	W078118
4,0	W078120



## AWS A5.17 Specification for Carbon Steel Electrodes and Flux for Submerged Arc Welding

The welding electrodes and fluxes covered by the specification are classified according to the following attributes:

- The mechanical properties of the weld metal obtained with a combination of a particular flux and a particular classification of electrode
- The condition of heat treatment in which those properties are obtained
- The chemical composition of the electrode produced with a particular flux.

### Classification Designators

FS XYZ-ECXXX	
F	Indicates a submerged arc welding flux
S	Indicates the flux contains crushed slag
X	Indicates the minimum tensile strength of weld metal made in accordance with the welding conditions given in the specification
Y	Designates the condition of heat treatment in which the tests were conducted. 'A' for as welded and 'P' for post weld heat treated
Z	Indicates the lowest temperature at which the impact strength of the weld metal meets or exceeds 27 J i.e. Z No impact requirements
	0      0°C
	2      -20°C
	3      -30°C
	4      -40°C
	5      -50°C
	6      -60°C
E	Indicates a solid electrode; EC indicates a composite electrode
XXX	Classification of the electrode used in producing the weld and given in the table below

### Chemical Composition Requirements for Solid Electrodes

Electrode Classification	%C	%Mn	%Si	%S	%P	%Cu
EL8	0,1	0,25 - 0,6	0,07	0,03	0,03	0,35
EL8K	0,1	0,25 - 0,6	0,1 - 0,25	0,03	0,03	0,35
EL12	0,04 - 0,14	0,25 - 0,6	0,1	0,03	0,03	0,35
EM12	0,06 - 0,15	0,8 - 1,25	0,1	0,03	0,03	0,35
EM11K	0,07 - 0,15	1,0 - 1,5	0,65 - 0,85	0,03	0,025	0,35
EM12K	0,05 - 0,15	0,8 - 1,25	0,10 - 0,35	0,03	0,03	0,35
EM13K	0,06 - 0,16	0,9 - 1,4	0,35 - 0,75	0,03	0,03	0,35
EM14K	0,06 - 0,19	0,9 - 1,4	0,35 - 0,75	0,025	0,025	0,35
EM15K	0,10 - 0,20	0,8 - 1,25	0,1 - 0,35	0,03	0,03	0,35
EH10K	0,07 - 0,15	1,3 - 1,7	0,05 - 0,25	0,025	0,025	0,35
EH11K	0,06 - 0,15	1,4 - 1,85	0,8 - 1,15	0,03	0,03	0,35
EH12K	0,06 - 0,15	1,5 - 2,0	0,2 - 0,65	0,025	0,025	0,35
EH14	0,10 - 0,2	1,7 - 2,2	0,1	0,03	0,03	0,35

### Example of AWS Classification:

F43 A2-EM12K is a complete designation for a flux-electrode combination. It refers to a flux that will produce weld metal which, in the as welded condition, will have a tensile strength of 430 to 560 MPa and Charpy V-Notch impact strength of at least 27 J at -20°C when produced with an EM12K electrode

under the conditions called for in this specification. The absence of an 'S' in the second position indicates that the flux being classified is a virgin flux.

Please note: AWS now makes provision for metric values. The specification containing equivalent metric values is indicated by AWS A5.17M

# Submerged Arc Fluxes

## Afrox HPF-A72 Submerged Arc Flux

Afrox HPF-A72 is an agglomerated flux with Mn and Si additions. HPF-A72 is a versatile flux with excellent weldability and easy slag removal; it is highly resistant to cracks and porosity and has a very good bead appearance. HPF-A72 is ideal for one-sided welding, double-sided welding, square edge joints, fillet welds and lap welds in structural and general engineering applications. It is recommended for welding inside grooves but is limited to material thicknesses below 25 mm. Due to the high oxidation potential, it does not require any special base metal preparation and cleaning prior to welding.

### Applications

Afrox HPF-A72 is used to weld gas bottles, truck wheels, structural shapes, pipes, joining plates, light boilermaking and parts with small diameters.

### Storage and Re-baking

The higher the basicity index of agglomerated fluxes, the more hygroscopic such a flux would be. All agglomerated fluxes should therefore be stored in conditions of less than 70% relative humidity. Welding with damp flux can cause porosity. Re-drying of flux suspected of being moist should be done for approximately two hours at about 300°C at a flux depth of about 25 mm. For many applications, it is not necessary to re-dry the flux.

### Classifications

AWS	A5.17/ASME SFA 5.17	F7A2-EM12K
-----	---------------------	------------

### Typical Chemical Analysis (All weld metal)

% Carbon	0,05	% Phosphorous	0,018
% Manganese	1,5	% Sulphur	0,025
% Silicon	0,8		

### Typical Mechanical Properties

Yield Strength	426 MPa
Tensile Strength	519 MPa
% Elongation	29
Charpy V-Notch at -29°C	23 J

### Flux Characteristics

Maximum Welding Current	1 000 A
Polarity	DC or AC
Welding Speed	1 300 mm/min

### Packing Data

Pack Mass (bags/kg)	Item Number
25,0	W071403

## Hobart SWX 110

Hobart SWX 110 are semi-basic agglomerated fluxes producing weld deposits with good mechanical properties at low temperatures. Hobart SWX 110 have excellent weldability, easy slag removal in deep grooves, good resistance to cracking and porosity and excellent bead appearance. Hobart SWX 110 flux can be used on multi-pass applications on unlimited thickness, with very little change in the chemical composition of the weld metal.

### Applications

Hobart SWX 110 can be used on structural steel, CrMo steel, high strength low alloy (HSLA) steels and quenched and tempered steels.

### Classifications

AWS A5.17/ASME SFA 5.17

F6A2-EL12	F7A2-EM13K
F7A2-EM12K	F8A2-EA 2-A2
F6A2-EM12K	F9A2-EA 3-A3
F7P2-EM13K	F9P2-EA 3-A3

### Storage and Re-baking

The higher the basicity index of agglomerated fluxes, the more hygroscopic such a flux would be. All agglomerated fluxes should therefore be stored in conditions of less than 70% relative humidity. Welding with damp flux can cause porosity. Re-drying of flux suspected of being moist should be done for approximately two hours at about 300°C at a flux depth of about 25 mm. For many applications, it is not necessary to re-dry the flux.

### Chemical Analysis (All weld metal)

	EM12	EM12K	EM13K	EA2	EA3	EB2	EM12KS	EM13KS
% Carbon	0,7	0,05	0,08	0,03	0,05	0,08	0,03	0,067
% Manganese	0,91	1,3	1,51	1,17	1,7	1,38	1,02	1,08
% Silicon	0,13	0,36	0,57	0,23	0,33	0,35	0,22	0,321
% Sulphur	0,03	0,022	0,019	0,03	0,021	0,013	0,009	0,011
% Phosphorous	0,024	0,02	0,015	0,03	0,029	0,019	0,012	0,015
% Molybdenum	-	-	-	0,52	0,58	0,4	-	-
% Chromium	-	-	-	-	-	1,0	-	-
% Copper	-	-	-	-	-	-	0,027	0,083

### Typical Mechanical Properties

	EM12	EM12K	EM13K	EA2	EA3	EB2	EM12KS	EM13KS
Yield Strength	393 MPa	426 MPa	410 MPa	499 MPa	565 MPa	655 MPa	408 MPa	430 MPa
Tensile Strength	476 MPa	519 MPa	525 MPa	577 MPa	655 MPa	720 MPa	490 MPa	530 MPa
% Elongation	30	29	30	2	26	23	27,8	26,5
Charpy V-Notch at -29°C	61 J	66 J	98 J	57 J	56 J	-	-	-
Charpy V-Notch at -18°C	-	-	-	-	-	51 J	-	-
Charpy V-Notch at -51°C	-	-	-	-	-	-	96 J	110 J
Charpy V-Notch at -62°C	-	-	-	-	-	-	56 J	84 J

### Flux Characteristics

Maximum Welding Current	800 A
Polarity	DC or AC
Basicity	1,4

### Packing Data

Pack Mass (bags/kg)	Item Number
25,0	W071401 (HPF-N90)
25,0	W071402 (HPF-N90F)

## Hobart SWX HF-N

Hobart SWX HF-N is totally neutral agglomerated flux, designed for welding with solid and tubular wires of the 400 series stainless steels. It can also be used with low alloy steel wires. It features clean slag removal with wires containing Nb and V, excellent recovery of the alloying elements from the tubular wires, such as Cr, Ni, Mo, Nb and V and accepts welding with twin-arc and oscillating technique, with currents up to 1 000 A. Hobart SWX HF-N flux should be used with wires containing at least 0,20% Si, in order to avoid porosity.

### Applications

The main application of Hobart SWX HF-N is the rebuilding of steel mill roll with tubular and solid wires of the 400 series stainless steels. It can also be used to rebuild shafts, wheels and journals.

### Storage and Re-baking

The higher the basicity index of agglomerated fluxes, the more hygroscopic such a flux would be. All agglomerated fluxes should therefore be stored in conditions of less than 70% relative humidity. Welding with damp flux can cause porosity. Re-drying of flux suspected of being moist should be done for approximately two hours at about 300°C at a flux depth of about 25 mm.

Typical Weld Metal Data												
Product	Composition of Weld Metal Deposited											Hardness HRC
	% C	% Mn	% Si	% S	% P	% Mo	% Cr	% Ni	% Nb	% W	% V	
Afrox TA887-S	0,12	1,0	0,6	0,01	0,015	1,5	12,5	2,5	0,15	-	0,2	40
Afrox TA8620-S	0,12	0,8	0,4	0,01	0,015	0,2	0,5	0,4	-	-	-	21
Afrox TA861-S	0,15	0,9	0,5	0,01	0,015	0,6	1,7	-	-	-	-	32
Afrox TA 242-S	0,14	2,0	0,8	0,01	0,015	0,7	3,0	-	-	-	-	40
Afrox TA258-S	0,34	1,2	0,5	0,01	0,015	1,5	6,0	-	-	1,4	-	54
Afrox TA410-S	0,08	1,0	0,6	0,01	0,015	-	12,8	-	-	-	-	36
Afrox TA A250-S	0,19	1,0	0,5	0,01	0,015	-	12,3	-	-	-	-	50
Afrox TA 865-SMod	0,18	1,1	0,4	0,01	0,015	1,0	13,5	2,3	0,15	-	0,15	48
WASA 414MM-S	0,15	0,9	0,5	0,013	0,022	1,2	12,5	2,0	0,17	-	0,18	42 - 45
Lincore ER423L	0,15	1,2	0,4	0,01	0,02	1,0	11,5	2,0	-	-	0,15	42 - 45
Stoody Thermaclad 423L	0,15	1,2	0,5	0,012	0,022	1,0	11,7	2,0	-	-	0,15	43 - 45
EB3	0,1	0,96	0,16	0,01	0,019	1,08	2,15	-	-	-	-	-
EM-12K	0,1	0,88	0,19	0,019	0,02	-	-	-	-	-	-	-

Packing Data	
Pack Mass (bags/kg)	Item Number
25,0	W071406

# Oxy-Fuel & Gas Welding Rods

## Afrox Copper Coated Rod (CCR)

A general purpose low carbon steel gas welding rod which is copper coated to reduce corrosion. It is recommended for oxy-acetylene welding of mild steel and is widely used in sheet metal work, the heating and ventilation industries, car body repairs, welder training schools and for low pressure piping and plumbing.

### Typical Chemical Analysis (All weld metal)

% Carbon	0,04 - 0,15	% Sulphur	0,035 max
% Manganese	0,35 - 0,60	% Phosphorous	0,04 max
% Silicon	0,03 max	% Copper	0,35 max

### Typical Physical Properties

Melting Range	1 490°C
Approximate Tensile Strength of Deposited Metal	386 MPa
Approximate Brinell Hardness	120 HB

### Brazing/Welding Parameters

Process	Oxy-acetylene
Flame Setting	Neutral
Flux	Not required

### Packing Data TIG (DC-)

Diameter (mm)	Consumable Length (mm)	Pack Mass (kg)	Item Number
1,6	750	5,0	W000040
2,5	750	5,0	W000045
3,2	750	5,0	W000041
5,0	750	5,0	W000042

## Mechanically Certified Consumables

Mechanically certified electrodes and wires are required by fabricators building and repairing components destined primarily for the petrochemical industry. Certification takes place in terms of the American ANSI/AWS A5.01 specification. A short description of the requirements is detailed below.

The certification of the consumable is based on two aspects:

- The lot classification
- The level of testing.

The consumables are broken into four primary groups:

- Coated manual metal arc electrodes
- Solid wires and rods

Classes					
<b>MMA Electrodes</b>	C1	C2	C3	C4	C5
<b>Solid Wires</b>	S1	S2	S3	S4	
<b>Cored Wires</b>	T1	T2	T3	T4	
<b>Fluxes</b>	F1	F2			

Generally, MMA electrodes produced by Afrox are manufactured to class C3, and MIG and TIG wires to class S1 and S3 respectively.

The definition for class C3 is:

A class C3 lot of electrodes is the quantity, not exceeding 45 000 kg, of any one size and classification (i.e. 7018-1) produced in 24 hours of consecutively scheduled production (consecutive normal working shifts). Class C3 electrodes shall be produced from covering (i.e. flux) identified by wet mix or controlled chemical composition and core wire identified by heat or cast number or chemically controlled composition.

The definition for class S1 is:

A class S1 lot of bare solid wires and rods is the manufacturer's standard lot, as defined in the manufacturer's QA programme (this in the case of Afrox is the heat or cast number which refers in terms of MIG 6000 and TIG 70S-6 to 100 000 kg of material).

The definition for class S3 is:

A class S3 lot of bare solid electrodes and rods, brazing and braze welding filler metal, and consumable inserts is the quantity of one size produced in one production cycle from one heat.

- Flux and metal cored wires
- Fluxes for submerged arc welding and brazing.

### Lot Classification (Class)

The lot classification basically specifies a number of aspects which take place during the manufacturing operation to closely monitor the quality and to be able to clearly identify a production batch of consumables. The classification system is given in the table below:

### Level of Testing (Schedule)

The level of testing is selected by the purchaser and there are six levels or schedules, i.e. F, G, H, I, J and K. The most commonly used for both electrodes and wires is Schedule I. Schedule I requires the following tests to be carried out and certified for MMA electrodes:

- Chemical analysis
- Tensile properties (i.e. 0,2% proof stress, tensile strength and % elongation)
- Charpy V-Notch impact properties
- X-ray soundness
- Moisture content (of the flux coating).

The purchaser would therefore specify consumables to be supplied in terms of for example class C3 schedule I or class C4 schedule J, etc.

A list detailing the Afrox products currently mechanically certified in terms of ANSI/AWS A5,01 is given in the table below:

Packing Data (7018-1)				
Diameter (mm)	Class	Schedule	Package Type	Item Number
2,5	C3	I	Box	W075282
3,15	C3	I	Box	W075283
4,0	C3	I	Box	W075284
5,0	C3	I	Box	W075285

**Packing Data  
(7018-1)**

Diameter (mm)	Class	Schedule	Package Type	Item Number
2,5	C5	K	Box	W087382
3,15	C5	K	Box	W087383
4,0	C5	K	Box	W087384
5,0	C5	K	Box	W087385

**Packing Data  
(MIG 6000 Cert)**

Diameter (mm)	Class	Schedule	Package Type	Item Number
1,0	S1	I	Box	W033912
1,2	S1	I	Box	W033913

**Packing Data  
(TIG 70S-6)**

Diameter (mm)	Class	Schedule	Package Type	Item Number
1,6	S3	K	Cardboard tube	W087501
2,0	S3	K	Cardboard tube	W087502
2,4	S3	K	Cardboard tube	W087503